

Bauxite beneficiation modifying factors

Caio van Deursen¹, Roberto Seno Jr.², Rodrigo Moreno³ and Thiago Franco⁴

1. Process Engineer 2. Bauxite and Alumina Technology Development Manager

3. Process Consultant 4. Process Engineer

Votorantim Metais

Corresponding author: caio.deursen@vmetais.com.br

Abstract

The Alumina Rondon project consists of a bauxite mine, beneficiation plant and an alumina refinery, along with its associated utilities and logistics. It will be installed in the Rondon do Para municipality in the Para state – northern Brazil. The refinery production capacity is three million tons of alumina per year. For this production, 12 million tons of ROM will be beneficiated, resulting in 9 million tons of washed bauxite (wet basis). The beneficiation process will occur in a single line plant at 1500 tons per hour. During the early stages of the project engineering, a characterization study was conducted. Such a study consists in the evaluation and quantification several key aspects of the material needed to proper equipment sizing. To confirm the values of the laboratory studies, an industrial test was done in the operating bauxite beneficiation plant installed in the Mirai municipality located in the state of Minas Gerais – southeast Brazil. The test was done with two bulk samples obtained from two pilot mines. The main aspects evaluated were: product loss, product contamination and effects of residence time in the scrubber.

1. Introduction

To produce aluminium, it is necessary to refine alumina. In the year of 2013 the total smelting grade alumina (SGA) production was 100 million tons. In the last ten years, the SGA production has doubled [1]. Alumina is refined from bauxite, and usual grades range from 35 % to 55 % of Available Alumina (AA). From the circa 200 million tons of bauxite annually refined nearly 20 % [2, 3] are from washed bauxite.

In the Bayer process, the Available Alumina (AA) contained in the bauxite is digested. Along with the AA digestion the Reactive Silica (RS) digestion also occurs. There are two sources of reactive silica (RS) quartz and kaolinite. Depending on the digestion temperature one or both might be digested. At 150 °C (or low temperature process) only the kaolinite is digested, at 250 °C (high temperature process) the digestion of quartz also occurs. After its digestion, the reactive silica precipitates as Desilication Product immobilizing Sodium Cations which will have to be replaced by the addition of NaOH – one of the main costs of Alumina production. Thus, the amount of NaOH makeup is directly related with the amount of reactive silica in the ore. So, for bauxite to be considered viable, the amount of AA must justify the consumption of NaOH by the RS. In a first approach, the ratio AA/SR (or module) must be higher than 10.

In this specific case, samples of the Rondon do Pará bauxite were analyzed. A typical sample from the ROM obtained from drill holes was analyzed. This sample had 33.9 % AA, 7.8 % RS with a module of 4.3. If this material is wet screened, in ideal conditions, the fraction coarser than 37 µm has 44.1 % AA and 2.5 % RS, with a module of 17.8. The fraction finer than 37 µm has 7.1 % AA, 21.6 % RS and a Mass Recovery (MR) of 27.7 % of the ROM. Table 1 summarizes the values.

This data justifies the beneficiation, i.e. the separation of the minus 37 µm for this specific bauxite. Kaolinite is a clay mineral and has a naturally fine particle size. The beneficiation process aims to reduce the particles size to expose or liberate the clay, disaggregate and separate it from the coarser particles. One point of attention is the comminution process: the separation is done by size, if this process is too intense, naturally coarser particles will be broken and separated as reject.

Table 1. ROM, Product and Reject grades, mass recovery and moisture (w/w).

	ROM %	Ideal Product +37 μm , %	Reject, %
AA	33.9	44.1	7.1
RS	7.8	2.5	21.6
MR	100	72.3	27.7
Moisture	12	12	25

Given the above, the mission of the processing plant is not the product grades or mass recovery, but to *efficiently separate the coarse particles from the fine ones*. The quality of this separation may be evaluated by the amount of natural coarse fraction lost to the reject (product loss) and the amount of natural fines present in the product (product contamination). The AA and RS grades are consequence of the natural qualities of the ROM or the process route, having the operation little influence on those values. The same applies to the product Mass Recovery (MR), as it is a natural characteristic of the ROM.

1.1 Beneficiation unit operations

The simplified flowchart of the Alumina Rondon beneficiation is shown in image 1.

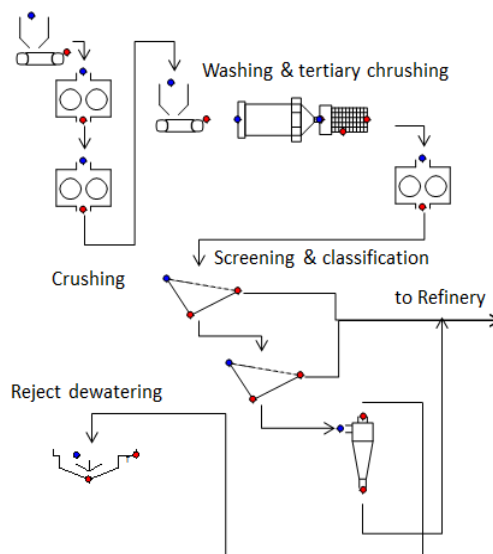


Figure 1. Alumina Rondon simplified beneficiation flowchart.

1.1.1. Crushing

The beneficiation of the Rondon do Pará bauxite begins when the mine trucks dump the material in the primary crusher hopper. This hopper may receive simultaneously material from six 32 ton trucks and a front-end-loader. The crushing area is the first step in the beneficiation process, and, as such, it must be able to handle the natural variability of the ROM: trucks dump intermittently and ore blocks vary in top size and size distribution. With that, the instantaneous capacity of the crushers must be high enough to deal with this variability and to form an intermediate stock pile to be consumed in case of a crushing shutdown.

The crushers selected for the Alumina Rondon beneficiation plant are sizer type crushers. These crushers have been successfully used in bauxite beneficiation, especially with the Amazon bauxite. They have several desired characteristics for bauxite processing, such as: self-cleaning

rotate at low speed, fine particles pass without being crushed, dynamically balanced, its dimensions are smaller than equipment with similar production rates, may be installed on rails, etc. These characteristics are beneficial to deal with some of the main bauxite processing issues by reducing problems with the material stickiness and over-crushing, avoiding product loss. The other characteristics save investments in building and ease maintenance.

The largest block expected from the mine should not exceed 800 mm, however, if a larger block is dumped into the primary crusher, its geometry and drive make the block rotate until it can be grasped by the teeth of the crusher. This type of event should be an exception, with the mining operation being responsible for preventing these blocks from being fed to crusher. Even though this is not detrimental to the equipment, it causes momentarily reductions in the production rate and should be avoided.

The product of the primary crusher shall not exceed 350 mm and this material will be directly fed into the secondary crusher which reduces the ROM to less than 75 mm. Since both equipments are low in height, they may be installed in the same building with the secondary just below the primary, thus reducing investments in new buildings. The supply of crushed product, in the event of crushing stop, will be maintained by the recovery of crushed material in the stockpile. The crushed material is sent to the washing, screening and classification plant.

1.1.2. Washing and tertiary crushing

The washing plant consists of a single equipment line (silo, scrubber, crushers and screens). The crushed material will be sent by a conveyor belt to a silo. The installation of the silo is necessary to stabilize the material flow sent by crushing. Under the silo, to control the flow to the scrubber, an apron feeder will be installed.

The drum washer or scrubber will be fed with crushed bauxite and water so that its product has 50% solids by weight. The scrubber is designed in a way that its main variables can be adjusted as needed by the process, that is, if the ROM has more or less clay, or is more or less thick, among others. This is possible by changing the flow of water to be fed into the scrubber, its rotating speed and the level of its discharge. The scrubber overflow is screened in an attached trommel with an opening of 40 mm and the oversize is fed into a pair of crushers. The tertiary crushing stage product should have a top size similar to the trommel aperture. Both flows are fed to the screening circuit.

1.1.3. Screening

The flow is fed to a 6 mm screen; the retained material will form the beneficiation product along with the retained from the next screen. The secondary screen receives the undersize from the primary screen and has an 840 μm aperture. The undersize of the secondary screen is fed to the classification circuit.

1.1.4. Classification circuit

The classification circuit receives the pulp from the secondary screen in tanks with 5 minutes of residence time. These tanks allow regulation of the flow thus minimizing variations in the percentage of solids in the flow fed to the cyclones. There are three cyclones batteries, each one receiving the underflow from the previous one in a rougher, cleaner and recleaner circuit. The objective of the cycloning circuit is to remove the fraction finer than 37 μm and with that, indirectly, increasing the AA grades and reducing the RS grades. The last cyclone underflow will be fed to a conveyor filter to be dewatered and will be deposited over the same belt that is carrying the coarser fraction. The cyclones overflow with the filtrate will be directed to the reject dewatering system.

1.1.5 Reject dewatering and disposal

The bauxite beneficiations reject or clay is the finest fraction of the ROM. The pulp containing these solids is fed into a thickener, the overflow is returned to the process water pond and the underflow is fed to a battery of press filters. The filters are composed of vertical plates covered with filter cloth. When they are "closed", the spaces between the plates are filled with pulp, filtering the water and forming a cake. This cake is pressed for further dehydration. In image 2 is shown the filtered reject cake.



Figure 2. Press filtered reject (minus 37 μ m fraction) at 75 % solids w/w.

This cake no longer drains water and will be charged with wheel loaders to the same trucks that brought the ROM. This level of dehydration allows this operation, once the stickiness of the material is considered low. As the processing mass recovery is approximately 70 %, circa one third of the fleet shall return to the mine with reject that will be deposited in mined out stripes. Once deposited, the mining cycle continues with the next strip overburden removal. The reject will assist in topographic reconstruction of mined areas. The filtrate is directed to the process water pond. From there this water is pumped back to the beneficiation plant.

1.1.6. Water

The ROM is fed into the beneficiation plant with 12% of moisture (water mass / total mass) and its product also has 12% of moisture. The reject, after mechanical dewatering, is sent back to the mine with 25% of moisture. The process outputs have more water than its feed and this makes water makeup needed.

1.2 Bauxite beneficiation proposed Modifying Factors

An 'Ore Reserve' is the economically mineable part of a Measured and/or Indicated Mineral Resource. It includes diluting materials and allowances for losses, which may occur when the material is mined or extracted and is defined by studies at Pre-Feasibility or Feasibility level as appropriate that include application of Modifying Factors. Such studies demonstrate that, at the time of reporting, extraction could reasonably be justified [4].

The Modifying Factors are considerations of mining, processing, metallurgical, infrastructure, economic, marketing, legal, environment, social and government conditions that impose changes in the resource once estimated.

In the specific case, the mineral resource was evaluated for AA and RS grades and washing mass recovery. Each of these variables was obtained by washing and testing the washed portion of each geological sample. The set of these results, after modelling, characterized the resource.

For the Alumina Rondon Mineral Reserve to be estimated, several Modifying Factors were applied to the Mineral Resource estimation. The beneficiation plant or processing plant modifies the resource in three ways:

1. Product loss;
Amount of material that the beneficiation plant should **have** recovered but did not, due to process imperfections
2. Product contamination; and
Amount of material that the beneficiation plant should **not have** recovered but did, due to process imperfections
3. Product recovery mesh.
The finest grain size considered product for the beneficiation plant.

The first and the second are correlated and are due to imperfections of sizing. The estimated loss in screening is irrelevant, since screens have physical limits that prevents coarser fraction to be present in the finer fraction (product loss). On the other hand some of the finer particles will be present in the screen oversize (product contamination). It is significant to state that contamination is the presence of the fraction that reduces the total AA grades and increases the RS grades, i.e. the minus 37 μm fraction.

In the classification circuit this effect is more relevant, since that, in this kind of separator, coarser particles have higher probability to be directed to the underflow and finer, to the overflow, but none have zero probability of being in either flow. In this way it is expected to find coarse particles in the reject and reject in the product flow.

The third Modifying Factor relies in the fact that the Mineral Resource was evaluated in 150 μm , that is, the geology drill hole samples were washed in this aperture and the AA and RS grades along with the mass recovery were estimated for this mesh. Since it is practical, in the processing plant, to recover material up to 37 μm , the reported mass and grades from the Mineral Resource also had to be modified by this factor. Thus increasing the mass recovery and re-evaluating the AA and RS grades.

2. Industrial test

In order to materialize what was designed in the basic engineering flow chart an industrial test was performed. The main objectives of this test were to measure the Modifying Factors resulting from bauxite beneficiation and to evaluate operational conditions.

The test was done with two bulk samples of what is going to be the ROM of the Alumina Rondon bauxite mine. The samples were obtained from two different pilot mines opened in the Rondon Norte plateau. The samples were mined in areas that represented the average characteristics of the material to be mined when the industrial operation is installed. Each sample had 1 000 tons and this mass was transported for 2 500 km to an operating beneficiation plant owned by Votorantim Metais in the municipality of Mirai.

The Mirai beneficiation plant is similar to what is projected for the Alumina Rondon beneficiation plant. Mirai's processing circuit start with two crushers in series, a primary and a secondary, a silo, a scrubber and two sets of screens. The screens oversize is the product. The secondary screen undersize, the material finer than 840 μm , in the Mirai beneficiation plant is discarded, differently from what will be done with the same fraction in the Alumina Rondon beneficiation plant.

The plant capacity depends on the feeding ore characteristics. The feed rate is adjusted by the screening quality; if the ROM has a higher content of fines the feed must be diminished. This is due to the screen capacity being proportional to the amount of undersize material. The main processing parameter is the residence time in the scrubber. Altering the residence time by altering the feed rate, is the most direct form to control the total energy applied to the ore. This energy is needed to disaggregate the clay from the coarser particles (product contamination), but too much energy comminute the material causing product loss. So that the beneficiating conditions of the projected Alumina Rondon plant are simulated,

the residence time in the scrubber was set to two conditions: four times the designed residence time (6 minutes) and the designed residence time (1.5 minutes).

With the first condition it was possible to evaluate the effects of *over-scrubbing* the bauxite. The expected product recovery was markedly higher than the one obtained in the six minute residence time test. The particles size distribution and grades evaluated from several samples obtained during the test proved that, not only the expected fine fraction was passing through the secondary screen, but also a significantly amount of the natural coarse fraction was comminuted and was passing through the 840 μm screen.

In the second test – feeding in a rate that resulted in the designed residence time – it was possible to observe the conceived operating conditions. The disaggregation happened visually as expected and the product samples indicated low contamination with clay.

Given that, in the Mirai plant, the beneficiation ends in the screens, it was not possible to test the classification circuit. However, particles classification, especially in cyclones, is a well-studied subject in the ore dressing discipline. So, with a well characterized feed, it is possible to simulate, at a high confidence level, the output of such a system. For the feed characterization several samples were taken during the industrial coarse circuit test.

3. Results and similar operations

During the industrial tests, several samples were taken from several points from the circuit as listed below:

- Primary crusher product;
- Secondary crusher product (or scrubber feed);
- Beneficiation product (taken from a conveyor belt that receives both oversizes); and
- Secondary screen undersize (or reject).

The first test lasted for four hours and the second, lasted for one hour. These samples were then analysed for particle size distribution and a mass balance was made. The coarse fraction (the screens oversize or product) mass recovery was evaluated by using the Equation 1:

$$\frac{\text{Product}}{\text{Feed}} = \frac{f - r}{p - r} \quad (1)$$

Feed Feed mass flow (dry tons per hour)

Product Product mass flow (dtph)

Reject Reject mass flow (dtph)

f conservative characteristic of the
feed flow (%) e.g. mass recovery
from a particular size fraction

p Characteristic of the product flow
(%)

r Characteristic of the reject flow (%)

This equation is widely used in several software for mass balancing, e.g. this equation is exposed in the JKSimMet v6 manual [5]. In this document is stated that: *size assays will work well around a size classifier such as a screen or a hydrocyclone, and elemental assays will work well around a flotation.* This equation was calculated for four size fractions listed in table 2 and results follow in table 3.

Table 2. Material PSD used as input for Equation 1.

Size (mm)	Feed (%)	Product (%)	Reject (%)
+6.35	48.5	73.3	0.0
-6.35 +0.840	16.6	23.6	2.1
-0.840 +0.037	14.7	1.5	41.5
-0.037	20.2	1.5	56.4
AA	33.7	41.5	22.6
RS	2.8	1.5	6.7

Table 3. Product mass recovery estimated by the Product / Feed equation with size assay and elemental assay.

Characteristic (mm or grade)	Mass Recovery or Product/Feed (%)
+6.35	66.2
-6.35 +0.840	67.4
-0.840 +0.037	67.0
-0.037	65.9
Average by size	66.6
AA	58.7
RS	75.0

The average mass recovery evaluated by Equation 1, 66.7 %, is one estimate for the specific bulk sample. As may be seen in Table 3, the values estimated by the size assay are more consistent with each other. The product mass recovery estimated by AA or RS grades are not well behaved. This might be explained by the fact that the process was done with a size classifier, not a grade classifier.

3.1 Samples mass

The minimum samples mass was defined using the equation 2 and 3 below [6]. These equations calculate, given a desired variance, particles mean diameter and other characteristics, the minimum sample mass.

$$IH_L \approx f \lambda \left[\left(\frac{1}{a_{Lc}} - 2 \right) d^2 + g d^2 \right] \quad (2)$$

$$M_s = \frac{IH_L}{S_{FE}^2} \quad (3)$$

IH_{L2} : Constitution heterogeneity, 23.3 g

f : Form factor, 0.5

λ : Particle density, 2.7 g/cm³

g : PSD parameter, 0.55 – calibrated PSD

a_{LC} : Relative amount of the size fraction, 45%

d : Particles mean diameter, $\frac{5 + 6.35}{2} = 2.8 \text{ cm}$

M_S : Sample mass

S_{FE}^2 : Specified variance, 5 %

The critical fraction for this study is the one with coarser particles, once $M_S \sim d^3$. The minimum sample mass for the -50.0 +6.35 mm fraction, which represents 45 % of the feed, is 9 kg, thus all samples taken had more than 9 kg.

3.2 Mass recovery by other approaches and evaluated contamination

The MR value predicted from the Resource Model [7] is **49.0 %**. This figure comes from evaluating several drill holes size and grades assays. This estimation is influenced by the values from drill holes executed in the vicinity of the pilot mine.

The mass recovery was also estimated by measuring the trucks mass in a road scale. This is the ROM and product masses after processing the Rondon do Pará Bauxite in the Mirai beneficiation plant. The measured values follow in table 3.

Table 4. Product mass recovery by road scale.

Feed mass	850.1 tons
Product mass	382.0 tons
Mass Recovery (%)	44.9 %

Still, for the coarse fraction, the screens oversize was laboratory washed and the total amount of minus 37 μm present in the product was, in the average of 15 samples, **1.7 % \pm 0.9 %** of its total mass, with no values exceeding **3.5 %**.

3.3 Alumina Rondon, MRN and Mirai

The Mirai plant screens have a similar ratio between their area and the solids flow considered in the second test as the Alumina Rondon screens and the project mass flow.

For the fine fraction, i.e. -840 +37 μm , the product loss was evaluated by modeling the Alumina Rondon cyclone circuit. By fitting the Nageswararao model with the project data – feed, densities, solids concentration and typical cyclones configurations for this operation - and comparing it to similar operations it was possible to estimate the product loss as 15 % (product mass lost to reject / initial product mass), once the contamination was set to 5 % (-37 μm mass in the product / recovered product).

Similar bauxite beneficiation operations, such as Mirai itself with the Zona da Mata ore and Mineração Rio do Norte (MRN) have typical operational product loss and contamination values as exposed in the table below 6 below.

Table 6. Product loss and contamination.

Operation	Product Loss	Product contamination
MRN	up to 5%	up to 5%

Mirai*¹*²

up to 3%

*¹ only coarse product.*² reconciliation program under development.

4. Discussion

The mass recovery evaluation for a short period of operation test depends heavily on the approach. The Product / Feed equation allows evaluating the relation with several size fractions, thus reducing the uncertainty.

This method is widely used when direct information about the flow is not available. The mass measured with the road scale is a direct measure of the mass fed and produced. However, since the test run for one hour (*short* period), the system loading had a high effect on the produced mass. It is estimated that the system loading time of the Mirai plant is about 20 minutes. This effect impacts the scrubbing phenomena. The first particles fed stayed inside the scrubber until it started to overflow. So they had to stay there for a longer period than the regimen period, thus receiving more energy and being comminuted specially by abrasion. This fact was observed by roundness of product particles, such as in Figure 3. It is expected that a freshly broken particle would have sharper edges that those seen in the example.



Figure 3. Roundness observed in an overscrubbed bauxite particle.

On the other hand, the mass recovery evaluated by the Product / Feed equation was higher than the one predicted by the Resource Model when the same mesh size recovery is analyzed. This may be explained by the fact that the Resource samples are from four inch (1016 μm) diameter drill holes, size quite different from the ROM top size found in the feed of the test, roughly 1.5 m.

Other fact that follows the same reasoning is that the Resource samples are crushed at one inch prior washing, while the beneficiation secondary crusher has a four inch top size.

The low amount of fines, 1.7 % (contamination) in the beneficiated product may be explained by the intensity of the scrubbing action when compared with the laboratory worker action over the laboratory screen. The scrubber is a 4 meter in diameter by 8 meter long equipment and the intensity of the scrubbing forces inside it are expected to be more intense than those applied by the laboratory worker.

As pointed out in the introduction, the ore grades by size fraction are exposed in Table 7.

Table 7. Ideal washing mass recovery and available alumina and reactive silica grades.

Size Fraction in μm	MR %	AA %	RS %
+840	60.4	44.2	2.6
-840 +100	8.1	45.2	2.2
Product or +100	68.5	44.3	2.5
-100 +37	3.8	41.0	1.7

-37 27.7 7.1 21.6

After the tests conducted and by using other operations as reference, the proposed Modifying Factors for the Rondon do Para beneficiation process are exposed in Table 8.

Table 8. Proposed Modifying Factors for the Alumina Rondon beneficiation plant.

Modifying Factor by size fraction	+840 μm	-840 +100 μm	-100 +37 μm
Product Loss	0 %	15 %	15 %
Product contamination	5.0 %	5.0 %	5.0 %
Product recovery mesh	-	-	3.8 %

The product loss is the amount of recoverable material that is not recovered in the process, the basis for its calculation is the initial amount.

The contamination is the presence of minus 37 μm in the evaluated size fraction and is measured in product basis, i.e. with 5 % contamination, there is 100 % recovered product. This means that the product (100 %) and contamination (5 %) adds to 105 % of the predicted mass.

The mesh recovery modifying factor was estimated by ultimate washing enough samples in several screen apertures and evaluating the grades obtained in each size fraction. By doing so it is possible to define up to which size the ore has economic grades.

The industrial plant should be designed to recover up to this size, independently of the resource model.

Using the exposed Modifying Factors the Ideal washing grades are modified to become the expected product of the beneficiation plant. These values are exposed in Table 9.

Table 9. Modified values after applying the Modifying Factors for the Alumina Rondon beneficiation plant.

Size Fraction in μm	MR %	AA %	RS %
+840	63.6	42.3	3.5
-840 +100	7.2	43.3	3.2
-100 +37	3.4	39.3	2.7
Product or +37	74.2	42.3	3.4
-37	25.8	9.6	20.2

The relative change is exposed in Table 10.

Table 10. Relative change between Ideal and Modified products.

Size Fraction in μm	MR %	AA %	RS %
Ideal	68.5	44.3	2.5
Modified	74.2	42.3	3.4
Relative change	+8.4	-4.6	+36.7

These tests increased the company's knowledge about bauxite beneficiation processing and ore dressing as a whole. More tests, varying feed rates and water ratios in the scrubber feed should be conducted to better understand the effects on residence time and rheology of the pulp inside the scrubber.

5. References

- 1 <http://www.world-aluminium.org/statistics/alumina-production/#data> - 21st July, 2014.
- 2 http://www.riotintoalcan.com/ENG/ourproducts/1803_weipa.asp - 21st July, 2014.
- 3 <http://www.mrn.com.br/en-us/operacao/sequencia-operacional/pages/default.aspx> - 21st July, 2014.
- 4 Australasian Code for Reporting of Exploration Results, Mineral Resources and Ore Reserves - JORC Code, 2012 Edition, Joint Ore Reserves Committee 2012.
- 5 JKSimMet V6 Manual, JKTech Pty Ltd, 2013
- 6 Pitard, Francis F. Pierre Gy's Sampling Theory and Sampling Practice, 2nd edition,
- 7 Mineral Resource and Exploration Department from Votorantim Metais, Relatório de Atividades e Avaliação dos Recursos Minerais das Lavras Piloto Norte e Sul – Platô Rondon Norte – Projeto Alumina Rondon, Aug. 2013.