

Performance Analysis of a Horizontal Anode Baking Furnace for Aluminum Production

Abdul Raouf Tajik¹, Tariq Shamim², Rashid K. Abu Al-Rub³ and Mouna Zaidani⁴

1. Ph.D. Student

2. Professor

3. Department Head and Associate Professor

4. Postdoctoral Researcher

Institute Center for Energy (iEnergy), Department of Mechanical and Materials Engineering,
Masdar Institute of Science and Technology, Abu Dhabi, U.A.E.

Corresponding author: tshamim@masdar.ac.ae

Abstract



Anode baking is the most expensive and the most important step during carbon anode production. The operational-geometrical parameters have significant influence on the anode baking furnace performance and carbon anode quality. Numerical modelling is an imperative tool to investigate the effect of different parameters on anode baking process. In the present study, a numerical model is developed which simulates heat transfer and flow distributions of the entire anode baking process. Using this numerical model, effect of various factors on anode temperature distribution is studied. Impact of degraded refractory-wall thermal conductivity on baking process is investigated and it is observed that for the aged furnaces this material properties degradation should be addressed accordingly. During the preheating and firing sections the temperature drops drastically from flue-gas to the center of the anode through the width of the pit which indicates a huge loss of energy. Calculating temperature standard deviation for the entire baking process, it is observed that the temperature non-uniformity presents mostly in the refractory wall and packing coke regions, and anode experiences a homogenous temperature distribution.

Keywords: Flue-wall; air infiltration; anode baking; volatiles combustion; packing coke.

1. Introduction

In aluminium industry, for each ton of aluminium to be produced approximately 0.4 ton of carbon anodes are consumed in the reduction cell. Green (unbaked) anodes should be baked (heat treated) in advance to obtain particular mechanical, thermal and electrical properties that make them suitable to be used as anode in the aluminium production process. The anode baking process takes generally 390-480 hours, and several phenomena occur during the process. Effects of operational-geometrical parameters on the performance of the furnace by plant tests are usually expensive and disrupt the baking process. Therefore, numerical-mathematical modelling is an imperative tool to study the effect of different parameters on the anode quality and furnace performance. Ultimately the optimum baking process and furnace geometry can be proposed. Several studies on modelling the anode baking process are reported in the literature [1-8]. The main objectives of the developed computational model are to study the effect of material properties on the baking process, to investigate the effect of various parameters on anode temperature distribution, and to investigate the temperature evolution through the width of the pit.

2. Model Description

Anode baking furnace is a circular kiln with pits, analogous to a closed chain. As shown in Figure 1, a fire group usually consists of three preheating sections, three firing sections, six

cooling sections, one unloading section, one or two sections for the loading of green anodes and one or two sections for the sake for maintenance. After each fire cycle time (typically 24-32 hours), the fire group equipment is displaced one section forward in the direction of the fire advance which is typically clockwise direction. A furnace comprises of two fire groups where the sections are arranged in two rows side by side, joined at the two ends by the crossover. The fire advance direction and the flow direction of combustion air and flue gases in the flue walls is the same. Simulating this intermittent movement of the fire group along with all the other simultaneous and transient phenomena involved in the baking process is very challenging and at the same time computationally very intensive since the initial and boundary conditions are continuously varying from one section to another. In a view to overcome this difficulty, all the sections from preheating, firing to cooling are treated as a whole and the baking furnace is assumed to be a semi-continuous counter flow heat exchanger between the stepwise movement of the solids in the pit and continuous flow of the gas in the flue. However, to avoid the virtual movement of the anodes, the solids are fictitiously subdivided into a number of finite slices along the length of the furnace. The velocity of the gas is varying and is determined by considering the local mass flow rate, temperature and pressure. The constant velocity of the solids is equal to a section length divided by the fire cycle time (about 5 m per day).

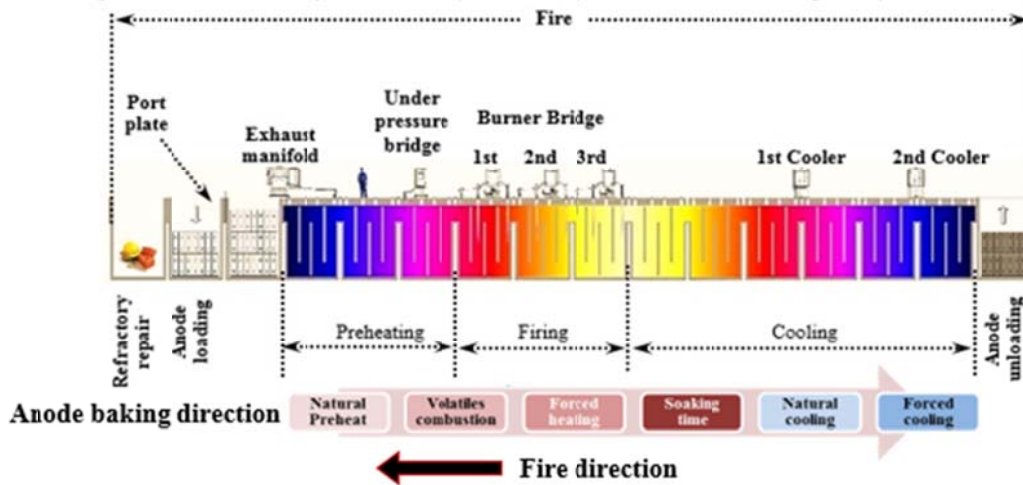


Figure 1. Longitudinal view of all the sections in a fire group [9]

2.1. Coupling of the flue and pit models

The transient nature of the anode baking process should be taken into consideration while developing the computational algorithms for the model. Assuming symmetry, only half of the flue and half of the pit can be considered for the computation. The time scale of the gas is much smaller than that of the solid materials (i.e. the solid components take more time to respond to changes in boundary conditions whereas gas responds to variations quickly). Combustion of fuel and volatiles in the flue along with gas flow combined with air in-leakage and ex-leakage can be modelled independent of time. However, the transient (time-dependent) heat conduction equation should be solved for the pit sub-model (i.e., heat transfer through the flue-wall, packing coke, and anode pack). Thus, the developed numerical model consists of two sub-models: flue and pit (flue-wall, packing coke, and anode pack). As shown in Figure 2, the pit model and flue model are developed separately and then coupled through an interface located at the refractory wall surface on the flue side.

6. References

1. R. Bui, A. Charette, T. Bourgeois, Simulating the process of carbon anode baking used in the aluminum industry, *Metallurgical Transactions B*, 15 (1984) 487-492.
2. R. Bui, A. Charette, T. Bourgeois, E. Darnedde, Performance analysis of the ring furnace used for baking industrial carbon electrodes, *The Canadian Journal of Chemical Engineering*, 65 (1987) 96-101.
3. R. Bui, E. Darnedde, A. Charette, T. Bourgeois, Mathematical simulation of a horizontal flue ring furnace, *Essential Readings in Light Metals: Electrode Technology for Aluminum Production*, Volume 4, (1984) 386-389.
4. R.T. Bui, A. Chartette, T. Bourgeois, A computer model for the horizontal flue ring furnace, *Industry Applications, IEEE Transactions on*, (1984) 894-901.
5. A. Charette, R.T. Bui, T. Bourgeois, Modeling the heat transfer in a ring furnace, *Industry Applications, IEEE Transactions on*, (1984) 902-907.
6. N. Oumarou, Y. Kocafe, D. Kocafe, B. Morais, J. Lafrance, A Dynamic Process Model for Predicting the Performance of Horizontal Anode Baking Furnaces, *Light Metals* 2015, 1079-1086.
7. L. Zhang, C. Zheng, M. Xu, Simulating the heat transfer process of horizontal anode baking furnace, *Developments in Chemical Engineering and Mineral Processing*, 13 (2005) 447-458.
8. D.S. Severo, & Gusberti, V., User-friendly software for simulation of anode baking furnaces, in: *Proceeding of 10th Australian conference*, 2011.
9. Akhtar, R. J., Meier, M. W., Sulger, P. O., Fischer, W. K., Friedrich, R., & Janousch, T. (2012). Anode Quality and Bake Furnace Performance of EMAL. *Light Metals*, 1175-1179.