

Chemical Compatibility of Geosynthetic Clay Liners to Aggressive Bauxite Liquor

Kuo Tian¹ and Craig H. Benson²

1. Research Scientist, Department of Civil and Environmental Engineering
George Mason University, Fairfax, VA, USA
2. Dean, School of Engineering and Applied Science
University of Virginia, Charlottesville, VA, USA.
Corresponding author: ktian@gmu.edu

Abstract

DOWNLOAD
FULL PAPER



Experiments were conducted to evaluate the effect of an aggressive bauxite liquor on the hydraulic conductivity of geosynthetic clay liners (GCLs) used for composite liners in disposal facilities for red mud from aluminum refining. Tests were conducted on two sodium-bentonite (Na-B) GCL and one bentonite-polymer (B-P) composite GCL. The Na-B GCLs contained powdered or granular bentonite. The B-P GCL contained a mixture of granular NaB and dry water-soluble polymer. All GCLs were prehydrated to 100% water content with a 2500 mg/L NaCl solution prior to permeation. The Na-B GCL with granular bentonite was permeable to bauxite liquor (5.0×10^{-10} m/s), whereas the Na-B GCL with powdered bentonite maintained low hydraulic conductivity (1.8×10^{-11} m/s). Hydraulic conductivity of the B-P GCL was very low initially (1×10^{-12} m/s), but increased over time to 1.3×10^{-10} m/s as polymer was eluted from the pore space. Clogging of fine pores by precipitates is hypothesized as the mechanism for the low hydraulic conductivity of the Na-B GCL with powdered bentonite. The findings indicate that GCLs used for composite liners in disposal facilities for residuals from aluminum refining can have very different hydraulic conductivity depending on the characteristics of the bentonite or bentonite-polymer mixture in the GCL. Construction specifications should ensure that the GCL that is installed is chemically compatible with the liquid to be contained.

Keywords: Geosynthetic clay liner, bauxite liquor, hydraulic conductivity.

1. Introduction

Geosynthetic clay liners (GCLs) are factory-manufactured clay barriers consisting of a layer of sodium-bentonite (Na-B) clay sandwiched between two geotextiles [1-3]. GCLs are widely used in waste containment facilities to limit leakage due to their low hydraulic conductivity to water (typically $< 10^{-10}$ m/s) and ease of installation [1-3]. The low hydraulic conductivity is due primarily to osmotic swelling of Na-B, which creates narrow and tortuous flow paths [1]. However, the propensity for osmotic swelling, and the hydraulic conductivity, are affected strongly by the chemistry of the liquid to be contained [4-6]. GCLs permeated with more aggressive leachates (higher ionic strength and/or a predominance of polyvalent cations) can be orders of magnitude more permeable than GCLs permeated with deionized (DI) or tap water due to lower osmotic swelling of the Na-B in the leachate [2-8].

Benson et al. [9] evaluated hydraulic conductivity of two conventional Na-B GCLs to a bauxite liquor from an aluminum refining operation with pH 12.2 and ionic strength of 774 mM. One GCL contained granular bentonite and the other powdered bentonite. Both GCLs had low hydraulic conductivity ($\sim 10^{-11}$ m/s) to tap water. When permeated with bauxite liquor, the hydraulic conductivity of the GCL containing granular bentonite was 1.8×10^{-8} m/s, whereas the hydraulic conductivity of the GCL with powdered bentonite was 2.5×10^{-12} m/s. The high hydraulic conductivity of the GCL with granular NaB was attributed to compression of osmotic swell by the bauxite liquor, resulting in large intergranular flow paths. Low hydraulic

conductivity of the GCL with powdered bentonite was attributed to precipitation of aluminum complexes in the fine pores of the bentonite powder.

This paper describes outcomes of tests conducted to evaluate the hydraulic conductivity of three commercially available GCLs being considered for a composite liner in a disposal facility for aluminum refining that will contain very aggressive bauxite liquor (pH 14.3, electric conductivity of 19.5 S/m). Tests were conducted on three different GCLs: two conventional Na-B GCLs (granular bentonite, powdered bentonite) and one bentonite-polymer (B-P) composite GCL.

2. Method and Materials

2.1. Geosynthetic Clay Liner

Physical properties of the GCLs are summarized in Table 1, with Na-BG corresponding to the GCL with granular bentonite, Na-BP to the GCL with powdered bentonite, and B-P for the GCL with a B-P composite. Both geotextiles on the GCLs were polypropylene, with the upper nonwoven and the lower woven. The geotextiles were bonded by needlepunching. Polymer loading in the B-P GCL was determined using the loss on ignition method.

Table 1. Physical properties of GCLs used in study.

GCL	Initial Thickness (mm)	Polymer Loading (%)	Swell Index in DI water (mL/2.0 g)	Swell Index in Bauxite Liquor (mL/2.0 g)
Na-BG	3.8	—	26.0	5.5
Na-BP	4.4	—	26.5	6.0
B-P	4.1	5.1	26.5	5.5

Note: Swell index measured using ASTM D5890 [10] in DI water and bauxite liquor. Polymer loading determined using loss on ignition test per ASTM D7348 [11]

Granule size distributions for the bentonites in the GCLs are shown in Fig. 1. The Na-BG GCL has medium-fine sand-size granules, the Na-BP has fine sand to silt-size granules, and the B-P GCL has medium sand-size granules. The Na-BP has 53% of the bentonite granules finer than the No. 200 sieve (75 μ m).

2.2. Bauxite Liquor

The bauxite liquor used in the testing program was obtained from an aluminum refinery. Analysis for elemental concentrations by inductively coupled plasma-optical emission spectroscopy (ICP-OES) showed that the predominant metals are Al (~107 mM) and Na (~1122 mM). The bauxite liquor has pH 14.3 and ionic strength of 2.05 M.

2.3. Prehydration

Prior to permeation, the GCL specimens were prehydrated to 100% water content by misting with a 2500 mg/L NaCl solution. Prehydration was anticipated to enhance chemical compatibility of the GCLs by inducing osmotic swelling of the bentonite and formation of a polymer hydrogel prior to contact with bauxite liquor [1].

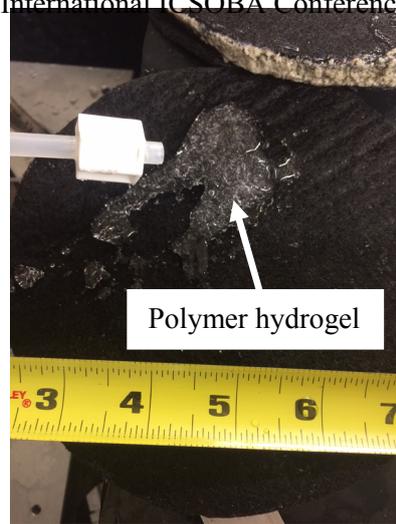


Figure 3. Removing polymer hydrogel clogging the effluent tube.

The initially low hydraulic conductivity of the B-P GCL is attributed to polymer clogging intergranular pores in the bentonite [3, 14]. The polymer forms a three-dimensional hydrogel structure that occupies the intergranular pore space when bentonite swelling is suppressed [2, 3], resulting in low hydraulic conductivity of GCL. However, during permeation, a sufficient mass of polymer was eluted, opening intergranular flow channels and resulting in higher hydraulic conductivity.

4. Conclusion

This study evaluated the hydraulic conductivity of three GCLs used in composite liners to contain bauxite liquor from aluminum refining. Three commercially available GCLs were evaluated - two with conventional sodium-bentonite (Na-B) and the other with a bentonite-polymer composite (B-P). One of the conventional GCLs contained granular bentonite and the other powdered bentonite. All three GCLs were prehydrated to 100% water content with 2500 mg/L NaCl solution prior to permeation.

Hydraulic conductivity of the Na-BG GCL containing granular bentonite increased immediately when permeated with bauxite liquor, with a final hydraulic conductivity of 5.0×10^{-10} m/s. The relatively high hydraulic conductivity of the Na-BG GCL to bauxite liquor is attributed to suppression of swell of the Na-B. In contrast, the Na-BP GCL with powdered bentonite had very low hydraulic conductivity (1.8×10^{-11} m/s) despite little swelling of the bentonite. The low hydraulic conductivity of the Na-BP GCL is attributed to precipitation of aluminum complexes in the fine pores of the powdered bentonite.

Hydraulic conductivity of the prehydrated B-P GCL to bauxite liquor initially was very low (1.0×10^{-12} m/s), but ultimately increased to 1.3×10^{-10} m/s. The low initial hydraulic conductivity of the B-P GCL is attributed to polymer hydrogel clogging intergranular pores that conduct flow in the Na-B GCL. The increase in hydraulic conductivity over time is attributed to polymer eluting from the pore space, resulting in larger intergranular pores to conduct flow.

The findings indicate that GCLs used for composite liners in disposal facilities for aluminum refining can have very different hydraulic conductivity depending on the characteristics of the bentonite or bentonite-polymer mixture in the GCL. Construction specifications should ensure that the GCL that is installed is chemically compatible with the liquor to be contained.

5. References

1. S. Bradshaw, and C. Benson, Effect of municipal solid waste leachate on hydraulic conductivity and exchange complex of geosynthetic clay liners. *J. Geotechnical and Geoenvironmental Engineering*, Vol. 140, No. 1, (2014), 04013038.

2. J. Scalia, C. Benson, G. Bohnhoff, T. Edil, and C. Shackelford, Long-term hydraulic conductivity of a bentonite-polymer composite permeated with aggressive inorganic solutions, *J. Geotechnical and Geoenvironmental Engineering*, Vol. 140, No. 3, (2014), 04013025.
3. K. Tian, C. Benson, and W. Likos, Hydraulic conductivity of geosynthetic clay liners to low-level radioactive waste leachate. *J. Geotechnical and Geoenvironmental Engineering*, Vol. 142, No. 8, (2016), 04016037.
4. H. Jo, T. Katsumi, C. Benson, and T. Edil, Hydraulic conductivity and swelling of non-prehydrated GCLs permeated with single species salt solutions. *J. Geotechnical and Geoenvironmental Engineering*, Vol. 127, No. 7, (2001), 557–567.
5. H. Jo, C. Benson, J. Lee, C. Shackelford, and T. Edil, Long-term hydraulic conductivity of a non-prehydrated geosynthetic clay liner permeated with inorganic salt solutions. *J. Geotechnical and Geoenvironmental Engineering*, Vol. 131, No. 4, (2005), 405–417.
6. D. Kolstad, C. Benson, and T. Edil, Hydraulic conductivity and swell of nonprehydrated GCLs permeated with multispecies inorganic solutions. *J. Geotechnical and Geoenvironmental Engineering*, Vol. 130, No. 12, (2004), 1236–1249.
7. C. Shackelford, G. Sevick, and G. Eykholt, Hydraulic conductivity of geosynthetic clay liners to tailings impoundment solutions. *Geotextiles and Geomembranes*, Vol. 28, No. 2, (2010), 206–218.
8. K. Tian, and C. Benson, Effect of low-level radioactive waste leachate on hydraulic conductivity of a geosynthetic clay liner. *Geosynthetics 2015*, IFAI, St. Paul, MN, USA, (2015), 236–244.
9. C. Benson, X. Wang, F. Gassner, D. Foo, Hydraulic conductivity of two geosynthetic clay liners permeated with an aluminum residue leachate. *GeoAmericas 2008*, International Geosynthetics Society, (2008).
10. ASTM D5890. Standard Test Method for Swell Index of Clay Mineral Component of Geosynthetic Clay Liners, ASTM International, West Conshohocken, PA, USA, (2011).
11. ASTM D6766. Standard Test Method for Evaluation of Hydraulic Properties of Geosynthetic Clay Liners Permeated with Potentially Incompatible Aqueous Solutions, ASTM International, West Conshohocken, PA, USA, (2012).
12. ASTM D7348, Standard Test Methods for Loss on Ignition (LOI) of Solid Combustion Residues, ASTM International, West Conshohocken, PA, USA, (2013).
13. C. Benson, A. Oren, W. Gates, Hydraulic conductivity of two geosynthetic clay liners permeated with a hyperalkaline solution. *Geotextiles and Geomembranes*, Vol. 28, No. 2, (2010), 206–218.
14. K. Tian, C. Benson, and W. Likos, Effect of anion ratio on hydraulic conductivity of a bentonite-polymer geosynthetic clay liner. *Proc., Geotechnical Frontiers 2017*, ASCE, Orlando, FL, USA, (2017), 10.1061/9780784480434.018.