

## **The Use of Red Mud and Kaolin Waste in the Production of a New Building Material: Pozzolanic Pigment for Colored Concrete and Mortar**

**Pedro Secco<sup>1</sup>, Elias Soares<sup>2</sup> and Márcio Barata<sup>3</sup>**

1. Master of Degree Student

2. School of Architecture and Urbanism Student

3. Assistant Professor

Postgraduate Program in Architecture and Urbanism

Federal University of Pará, Belém, Brazil.

Corresponding author: marciobarata@ufpa.br

### **Abstract**

The state of Pará is one of the greatest producers of mineral substances in Brazil. Kaolin for paper coating industry and bauxite for alumina and aluminium production are amongst the most important commodities. The latter is responsible for the generation of red mud, a well-known residue from Bayer process. The kaolin processing plants are also responsible for the generation of large amounts of wastes, in this case, very fine-grained kaolinite (white mud). The research aimed to find a final destination for such residues by developing new building materials. The proposed material is a pozzolanic pigment produced through calcination and grinding of mixtures of red mud and kaolin waste. The pozzolanic pigments provided increased mechanical strength and color stability of the colored mortars relative to the inert pigment. The pozzolanic characteristics of the pigments reduced the leaching of the mortars. The new material has proven to be promising in its application as an innovative construction material, with the possibility of opening a market that has not been explored in Brazilian civil construction: the colored mortars and concrete.

**Keywords:** Red mud, kaolin waste, colored concrete, pozzolanic pigment.

### **1. Introduction**

The state of Pará is one of the most privileged regions of the planet in terms of exploitation of mineral resources. The mining projects in Pará stand out because of the quality of the product, the commercialized values and the magnitude of the production volumes, which makes them also responsible for the generation of significant quantities of waste or by-products released and deposited in the environment. Among the most diverse types of residues generated from its intense mineral activity, the production volume of the kaolin waste (KW), due to the extraction and processing of kaolin, and the red mud (RM) of the Bayer process to obtain alumina from bauxites. It is estimated that the deposited amounts of KW and RM since the implantation of kaolin mills and Alumina do Norte do Brasil SA (ALUNORTE) are 15 and 60 million tons, respectively.

The KW has excellent technical characteristics, which has been demonstrated by the various researches, indicating the application potential not only in the field of building, but also in the refractory and advanced ceramic industries [1-7]. It consists essentially of extremely fine kaolinite, presents excellent uniformity and easy handling. All these requirements are excellent for the production of a highly reactive pozzolan from the calcination and grinding of pure kaolinite clays with very low inert minerals called metakaolin or metakaolinite.

RM itself would not be a toxic waste if it were not for its causticity, so much so that the United States Environmental Protection Agency does not classify it as a hazardous waste [8]. However,

other researchers consider it to be toxic precisely because of the high alkalinity and ion exchange capacity, which constitute a high risk to neighboring populations [9-10]. The chemical and mineralogical characteristics of RM impose difficulties to its use due to the variety of minerals present. In general, RM consists of a complex assembly of minerals ranging from those not dissolved in the process such as aluminum oxides and hydroxides (gibbsite, boehmite e diaspore), the iron oxides and hydroxides (hematite e goethite), rutile, anatase, calcite, dolomite, kaolinite, besides the neo-formed ones as sodalite and cancrinite and others that are in the form of traces as the oxides of V, Ga, P, Mn, Mg, Zn, Th, Cr e Nb.

In addition to the trend in the world aluminum industry for the densification of waste in order to reduce the generated volume of RM, many attempts have been made to take advantage of it instead of simply depositing it because of the high costs of RM disposal in the residue disposal area (DSR). However, the vast majority of the studies did not find a satisfactory application from the economic point of view [11]. Among the various applicability of RM, it is important to highlight the direction of the efforts for the use in Construction as a raw material for the manufacture of building materials. The feasibility of such a solution would be of threefold benefit, since the large-scale consumption of building materials could substantially eliminate or mitigate the problem of waste disposal; would add economic value to RM and would be easier to deploy on a universal scale.

Perà et al [12] claim that calcined RM could be used to produce colored concrete as a low-cost pigment compared to conventional pigments. In addition to the economic aspect, it presents some other technical advantages such as the elimination or reduction of efflorescence, common pathology in concrete structures and that is extremely harmful to concrete and colored mortars because it is responsible for the appearance of efflorescence on the surface, substantially damaging the color of the material surface [13]. Another positive aspect would be the possibility of being used in larger percentages, without loss of resistance, which commonly occurs with conventional inorganic pigments, which are inert.

A disadvantage of the use of RM as a building material would be free or exchangeable sodium present in sodalite, which could render its use in Portland cement based products unreliable due to the activation of alkali-aggregate reactions and the crystallization of salts on the surface (efflorescence). Due to this possibility, the present paper starts from the hypothesis that the combined calcination of RM with KW, in addition to increasing the pozzolanic activity, the exchangeable sodium present in the sodalite can be stabilized by solidification (S / S) when the occurs the formation of the structure of silicates and calcium aluminosilicates from the cement hydration and the pozzolanic reactions between metakaolinite and Portland cement.

Another advantageous aspect of the combined use of KW and RM are the distances between the residue disposal areas. Both residues are generated in the municipality of Barcarena, within a radius of 5 km between the DSR of ALUNORTE and the sedimentation ponds of Imerys. The aim of this article was to evaluate the technical feasibility of the pigments from the RM and KW mixtures by investigating their effect on the properties of colored mortars such as compressive strength, color stability and, finally, to contribute to an environmental assessment of RM by conducting leaching tests on the pigments and mortars that incorporated these pigments.

## **2. Experimental**

### **2.1. Raw materials and pigments**

The raw materials used in the research were KW from Imerys and RM from ALUNORTE. The pozzolanic pigments were produced from calcination at 800 °C and milling of three distinct proportions of RM and KW, besides the individually calcined RM (CRM). The commercial

pigment adopted as reference was Bayerferrox 120® (BF). Table 1 shows the composition of the pozzolanic pigments investigated in the experimental program.

**Table 1. Pozzolanic pigments investigated in the experimental program.**

Pozzolanic Pigment	% RM	% KW
RK19	10	90
RK55	50	50
RK91	90	10
CRM	100	0

The mineralogy of the raw materials and the pigments was evaluated by X-ray diffractometry (XRD) by the powder method (model *Empyrean*, PANalytical). The chemical characteristics of the raw materials were carried out using energy dispersive X-ray fluorescence spectrometry (EDS, Model 700 HS, Shimadzu). The particles size distribution of the RM and KW obtained by laser grain size measurements (CILAS Model 715 E 701). The specific surface obtained of the raw materials was measured using the BET method (Micromeritics ASAP 2020). The densities of RM and KW were determined according to the requirement of Brazilian standard NBR 16.605.

## 2.2. Mortars mix proportions

The mortars were produced with structural white Portland cement from the Mexican company CEMEX, equivalent in Brazil to CPBE 32. The fine aggregate was a silica natural sand (density 2.65 kg / dm<sup>3</sup>, absorption 0.8 % and fineness modulus 2.4). The superplasticizer additive used was Glenium 51®, polycarboxylate ether based, with a mean density of 1.05 g / cm<sup>3</sup>.

Mortars were produced according the binder to sand ratio of 1:3.5 (in mass) and a water/binder ratio kept constant of 0.55. Six mortar were molded, one relative to Portland Cement (controle mix) and five with 10% substitutions of the cement by the pozzolanic and commercial pigments (CRM mix, RK19 mix, RK55 mix, RK91 mix and BF mix). In mortars with 10% of pigments the superplasticizer additive (polycarboxylate ether based) was used. A seventh mortar with 10% cement replacement per calcined KW was cast exclusively for the leaching test on mortars (CKW mix).

## 2.3. Methods

The compressive strength was carried out in mortars in accordance with the procedures described in Brazilian standard NBR 7215. All the mortars samples were cast into 50 x 100 mm cylinders for the determination of compressive strength at 1, 7 and 28 days. For each age, three samples were molded, totalizing 12 specimens for each type mortar. After casting, all the samples were placed in the laboratory environment at 23.0 ± 2.0 °C for 24 hours. After that, the molds were removed and the mortar specimens were stored in saturated lime water as specified in NBR 7 215 until the time of testing.

The environmental assessment of dry RM and pozzolanic pigments was carried out through leaching test described in Brazilian standard NBR 10 005. The environmental assessment of mortars produced with pozzolanic pigmentos was carried out according to the Dutch standard [16]. The test consisted in immersing cylindrical specimens of mortar of dimensions 50 x 100 mm at the age of 28 days in acrylic tanks and covered by lixiviant (liquid/solid = 5). Acidified demineralize water (pH close to 4) was used at each renew lixiviant. After 64 days, the leachate extract obtained was filtered through a 45 µm membrane and identified by inductively coupled plasma - optical emission spectrometry (ICP - OES) (Varian, model VISTA MPX CCD

simultaneous). These analyzes were restricted only to control mortars and with a 10% substitution of CRM, RK91, RK55 and RK19.

The color provided by pigments to Portland cement mortars and their stability to the natural and controlled environments were evaluated by colorimetry. The color was determined using the CIELAB color space [14-15], from the initial and final  $L^*$ ,  $a^*$ , and  $b^*$  values were obtained using a Konica Minolta spectrophotometer, model CR-400. To assess the color stability, the total color-difference parameter ( $\Delta E$ ) was calculated using successive measurements performed at different times. This work used the results from the CIEDE1976 ( $\Delta E_{76}$ ) [16-17]. The color-difference ( $\Delta E_{76}$ ) between the  $a$  and  $b$  points in an object is the Euclidian distance between the color stimulus in both points, and approximately represents the color-difference perceived by the color stimulus in the CIELAB color space. The Equation (1) calculates this vector magnitude.

$$\Delta E_{76}^* = [(\Delta L^*)^2 + (\Delta a^*)^2 + (\Delta b^*)^2]^{1/2} \quad (1)$$

where:

$$\Delta L^* = L_b^* - L_a^*$$

$$\Delta a^* = a_b^* - a_a^*$$

$$\Delta b^* = b_b^* - b_a^*$$

In both laboratory and field analyzes, chromatic measurements were performed for the ages of 1 and 238 days. In these tests, six prismatic specimens of 100 x 100 x 30 mm dimensions were molded for each type of mortar, three for control environment and three for exposure to natural environmental in the Amazon region. In the laboratory, the specimens were under controlled conditions of temperature and humidity, in the case  $65 \pm 5\%$  and  $23 \pm 2^\circ\text{C}$  respectively. In the field, the specimens were submitted to conditions of the equatorial rainy climate of Belém, remaining in this natural environment for approximately eight months, covering the dry and rainy seasons. For each specimen, six color measurements were performed on the surface of 100 x 100 mm<sup>2</sup>. The value of the chromatic variation  $\Delta E_{76}$  per mortar specimen was obtained from the mean of these six measurements. To ensure that the measurements always occurred at the same points of the specimens, a mask with horizontal and vertical quadrants (2 x 2 cm<sup>2</sup>) was made.

### 3. Results and discussion

#### 3.1. Characterization of raw materials and pigments

The physical and chemical characteristics of RM and KW are shown in Table 2. The Figures 1-2 show the x-ray diffractograms of raw materials and pigments. RM is composed of hematite and goethite, besides gibbsite, anatase and sodalite. Fe present is in the form of hematite ( $\text{Fe}_2\text{O}_3$ ) and goethite ( $\text{FeOOH}$ ), both responsible for the intense red color of the RM.  $\text{Al}_2\text{O}_3$  present in the RM is in the form of aluminum hydroxide of the gibbsite type ( $\text{Al}(\text{OH})_3$ ) as well as in the crystalline structure of sodalite ( $\text{Na}_{7,6}(\text{Al}_6\text{Si}_6\text{O}_{24}) \cdot (\text{CO}_3)_{0,93} \cdot (\text{H}_2\text{O})_{2,93}$ ), newly formed mineral during the bauxite digestion process.  $\text{SiO}_2$  and  $\text{Na}_2\text{O}$  present in RM are also part of the structure of sodalite.  $\text{TiO}_2$  is in the form of anatase and  $\text{CaO}$  is part of the structure of calcite. The high content of Fe explains the high density of 3.00 kg / dm<sup>3</sup> of RM. Another relevant aspect is the high concentration of sodium, either free or weakly bound to the sodalite structure, which can cause problems related to surface efflorescence if the RM is incorporated in the production process of building materials.

The KW consists essentially of a well crystallized kaolinite with a low degree of defects, with sharp high intensity peaks at angles  $2\theta$  de  $12,46^\circ$  e  $25,05^\circ$  and triplets with well individualized

reflections. When it is calcined, the crystalline structure is disordered, being identified in the x-ray diffraction as an amorphous band between the angles  $2\theta$   $10^\circ$  e  $30^\circ$  (Figure 2).

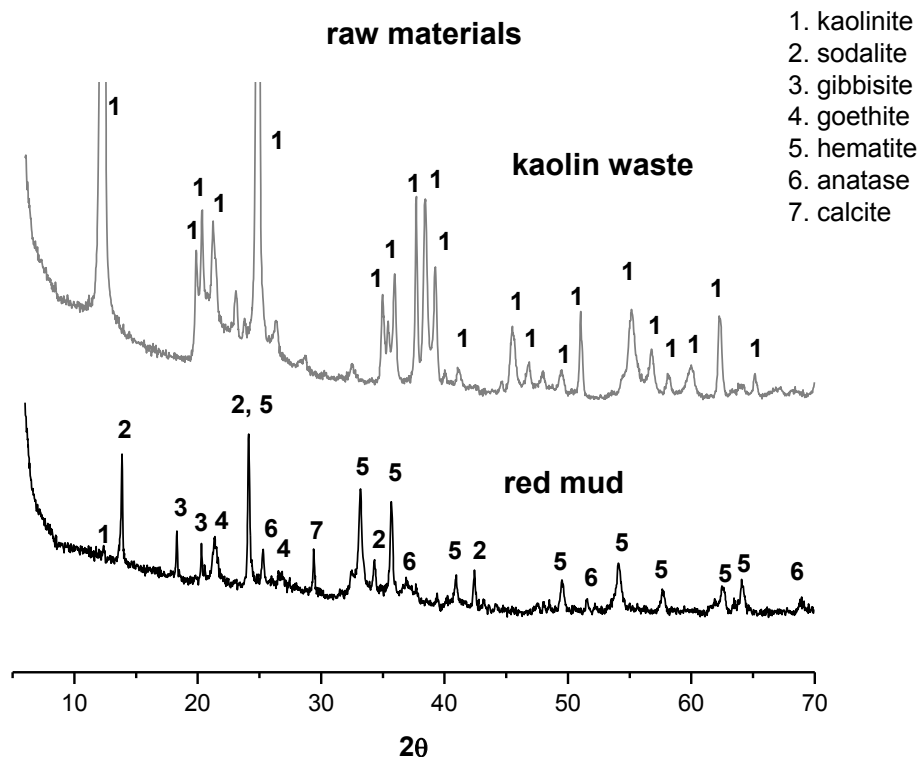


Figure 1. X-ray diffractogram of raw materials.

Table 2. Physical and chemical characteristics of RM and KW.

Parameters	RM	KW
SiO <sub>2</sub>	18.48	45.27
Al <sub>2</sub> O <sub>3</sub>	23.26	39.24
Fe <sub>2</sub> O <sub>3</sub>	31.89	0.57
TiO <sub>2</sub>	6.91	0.45
Na <sub>2</sub> O	11.58	0.21
K <sub>2</sub> O	0.11	< 0.05
CaO	1.55	< 0.05
MgO	0.10	< 0.05
MnO	0.19	< 0.05
P <sub>2</sub> O <sub>5</sub>	0.09	0.08
LOI	5.85	14.12
Density (kg / m <sup>3</sup> )	3.05	2.55
BET specific surface (m <sup>2</sup> / g)	15.0	18.0
D <sub>50%</sub> (μm)	3.0 – 4.0	3.0 – 6.0

In the RM calcined at 800 °C, the gibbsite disappeared; however, the presence of boehmite or  $\gamma$ -alumina which are the minerals formed from the dehydration of gibbsite at temperatures above 300 °C were not identified. Possibly because of the low amount and the high background in the X-ray diffractogram of RM. These hydroxides and aluminum oxides are the pozzolanically

active phases in RM. The goethite became hematite, intensifying the red color of the RM. The sodalite decomposed and from this process alkaline oxides of the denser structure of the type  $\text{NaAlSiO}_4$  and  $\text{Na}_5\text{Al}_3\text{CSi}_3\text{O}_{15}$  were formed. Anatase and quartz traces were also detected.

The pozzolanic pigments from the mixtures of RM and KW (RK91, RK55, RK19) are composed of the same minerals of the CRM (hematite,  $\text{NaAlSiO}_4$ ,  $\text{Na}_5\text{Al}_3\text{CSi}_3\text{O}_{15}$ , quartz and anatase), as well as metakaolinite from KW incorporated into RM. The latter is the phase responsible for the pozzolanic activity of these pigments. The difference in the mineralogical composition of the pigments results from the higher or lower concentration of hematite or metakaolinite, depending on the type of pigment. The commercial pigment BF, as expected, is composed only of hematite, well crystallized, with high intensity, inherent in the controlled production process of this material (not shown).

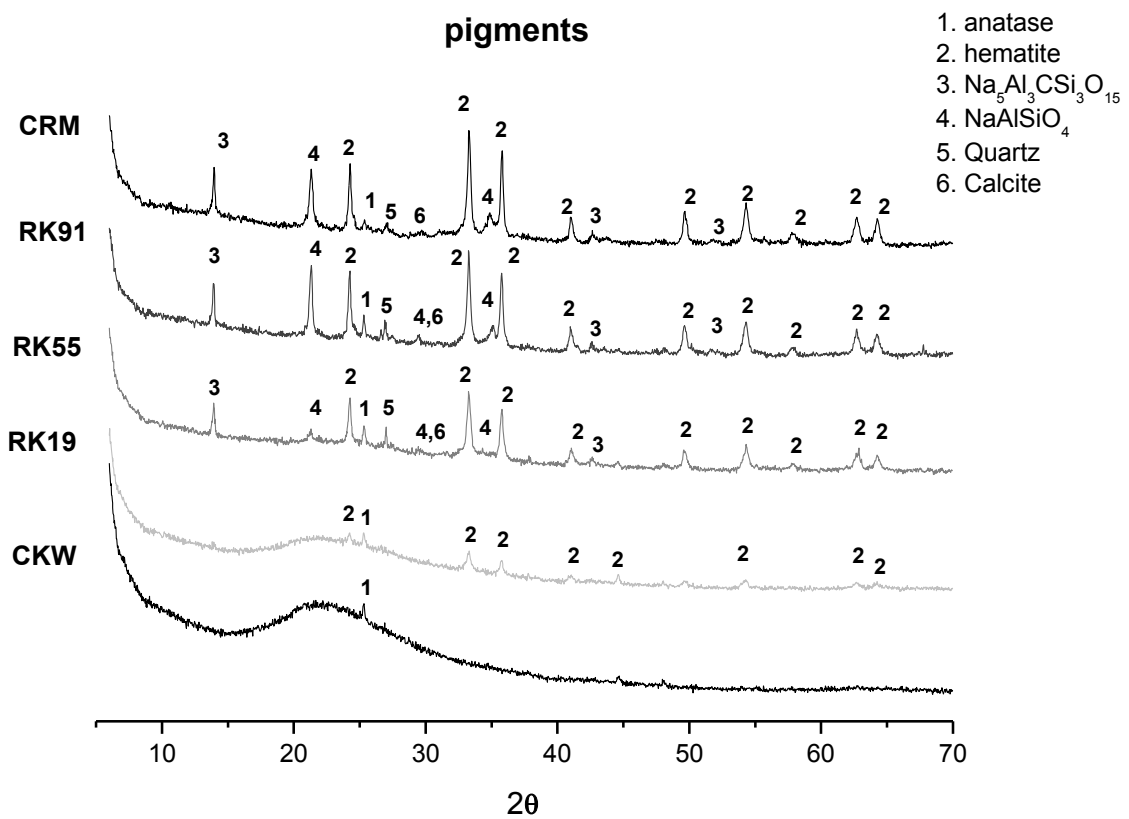


Figure 2. X-ray diffractogram of pigments.

### 3.2. Compressive strength

Figure 3 shows the development of compressive strength of reference mortar and with 10% of pigments. Figure 4 shows the relative compressive strengths compared to PC mortars for the ages of 1, 7 and 28 days. The mortars RK55 and RK19, with higher kaolinite incorporations in the pigments, 50 and 90%, respectively, presented the highest strengths for all ages observed. Os acréscimos variaram entre 11 e 86% e são atribuídos à alta reatividade da metacaolinita. The metakaolinite present in the pigments RK19 and RK55 reacts with the calcium hydroxide from the hydration of the cement to form new products such as stratlingite (or hydrated gehlenite), of

lower density than the C-S-H formed in the ordinary Portland cement paste (reference), providing in this way greater filling of the voids in the cement matrix, which results in greater mechanical strength and pore refinement.

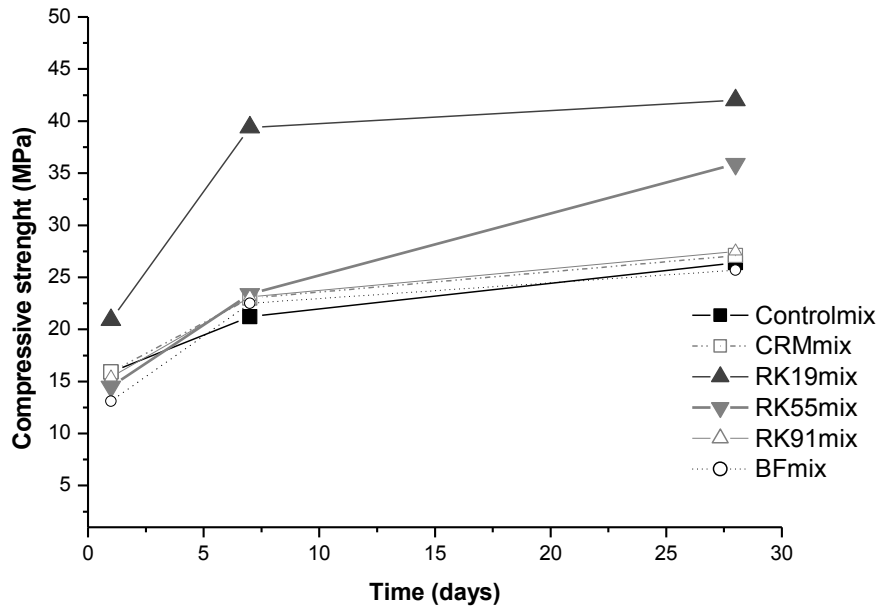


Figure 3. Compressive strength of mortars at 1, 7 and 28 days.

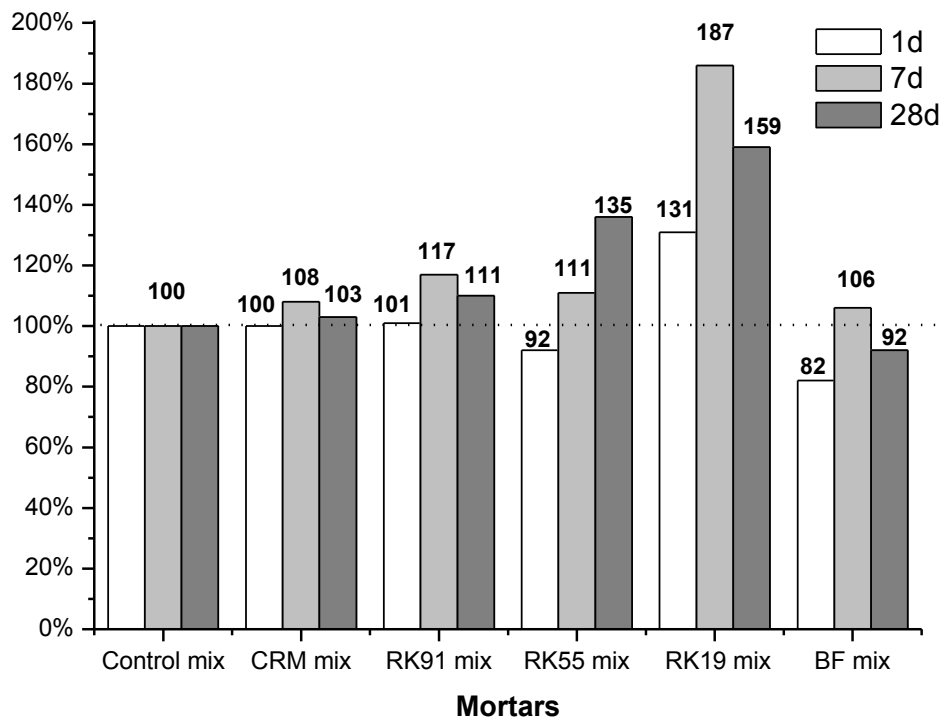


Figure 4. Compressive strength of mortars normalized to the strength of control mix.

The mortars with calcined RM and predominance of RM in the composition (RK91) also presented higher compressive strengths than the reference mortar and BF. However, the increases were smaller than those obtained with RK19 and RK55 mortars, between 1 and 17%. The increased resistance presented by these mortars is due to the pozzolanic and filler effects of RM. In the case of the pozzolanic effect, although it is lower than that of kaolinite, it is attributed to the hydroxides and aluminum oxides present in gibbsite. The filler effect is caused by the very fine RM particles which accelerate the hydration reactions of the cement, providing a substantial surface increase for the nucleation of new hydration products. However, this effect occurs more pronounced in the first 24 hours, whereas for later ages the pozzolanic effect is more preponderant. For this reason, the increase in compressive strength of CRM and RK91 mortars at the ages of 7 and 28 days is not as pronounced as for RK19 and RK55 mortars because of the low pozzolanic activity of RM.

In relation to the commercial pigment BF, the incorporation of 10% on the Portland cement caused a loss of mechanical resistance in relation to the reference mortar. This is attributed to the fact that it is an inert mineral admixture, which does not react with Portland cement.

All pigments from the RM and KW mixtures provided significant increases in compressive strength for all ages evaluated, which means that they can replace the cement in percentages even greater than 10% without loss of strength mechanical and even increase the color tonality of mortars and concrete products. The difference between these pigments and BF is that they are pozzolanic, in other words, capable of reacting with Portland cement.

### **3.3. Environment assessment**

The concentration of heavy metals leached from dry RM, pozzolanic pigments and white Portland cement are shown in Figure 5. The results show that dry and calcined RM as well as pozzolanic pigments are classified as non-hazardous waste (Class II) because the contents not exceed the limits established in annex F of the Brazilian standard NBR 10004.

The leached elements of the mortars are shown in Figure 6. All mortars produced, with or without pigments, had concentrations below the limits defined in annex F of the Brazilian standard NBR 10004. These results are a consequence of the previous ones, taking into account that neither the pigments nor Portland cement had concentrations above the established maximum limits.

The concentrations of sodium leached from the pigments obtained in the test as well as the theoretical values calculated from the weighted average of the sodium contents of each of the dry raw materials (RM and KW) are shown in Table 3. The sodium leached content of RM is 152 mg / L. However, when calcined alone there was a 13% reduction of sodium in the leached extract. Calcination was responsible for the conversion of sodalite to alkali oxides of more compact structures such as  $\text{NaAlSiO}_4$  e  $\text{Na}_5\text{Al}_3\text{CSi}_3\text{O}_{15}$ , which probably reduced the sodium ion exchange capacity. The pozzolanic pigments also showed reduction of the leached sodium determined in the test compared to that calculated from the percentages of dry raw materials. The reduction range varied between 10 and 40%, indicating that during the firing the incorporation of kaolinite increased the conversion of sodalite to alkaline oxides of dense structure.

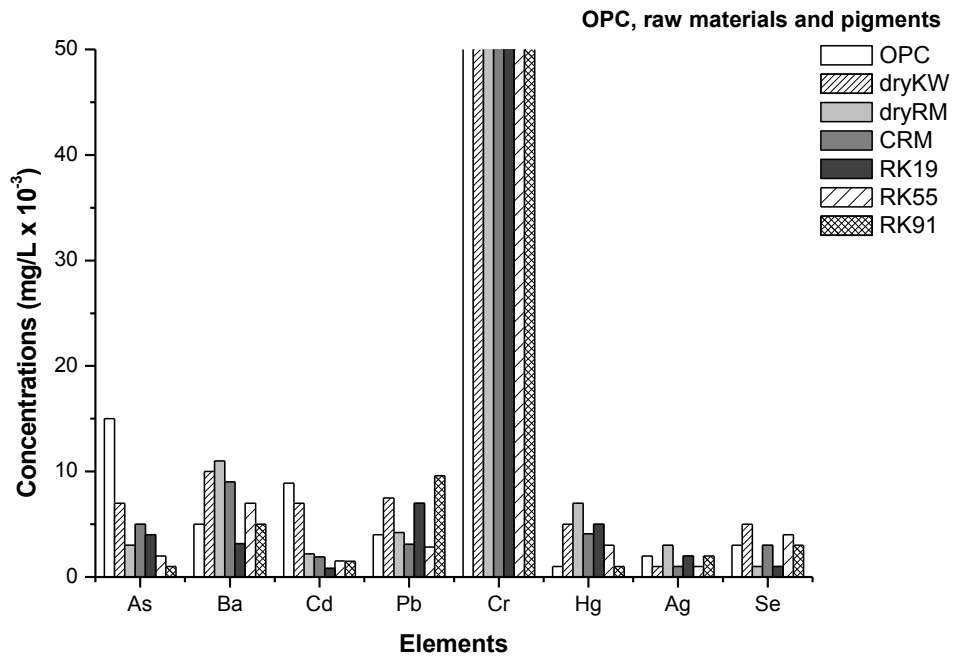


Figure 5. Concentrations of elements leached from raw materials, cement and pigments.

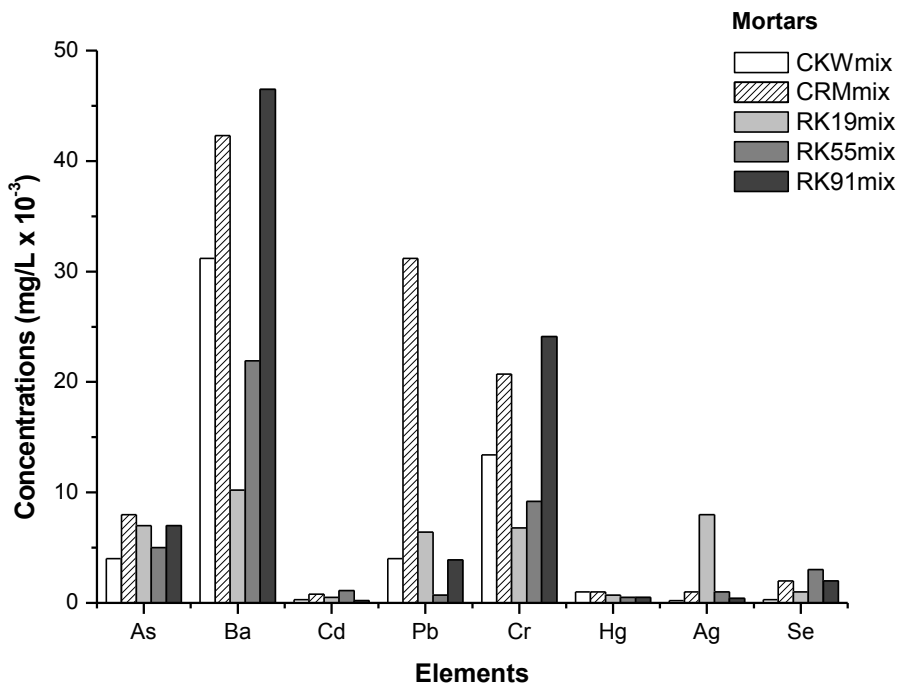


Figure 6. Concentrations of elements leached from mortars.

The concentrations of sodium leachate from the mortars determined in the test and the theoretical values calculated from the weighted average of the sodium contents of the calcined

RM and KW calcined mortar are shown in Table 4. The concentrations of sodium in the leached extract of the mortars with the pozzolanic pigments were lower than those calculated from the individual concentrations of each of the calcined RM and KW mortars. The reductions in sodium concentration varied between 22 and 58%, being the highest for mortars with the highest percentages of metakaolinite (RK55 and RK19). The results show that sodium was stabilized by solidification (S / S) from the formation of the structure of silicates and calcium aluminosilicates from the pozzolanic reactions between metakaolinite and Portland cement. The incorporation of KW to RM not only brought benefits to the mechanical properties but also allowed the encapsulation of the free sodium present, reducing the efflorescence phenomenon.

**Table 3. Concentrations of sodium leached from the pigments obtained in the test as well as the theoretical values.**

Pigments	Na <sub>test</sub> (mg / L)	Na <sub>theoretical</sub> (mg / L)	Reduction (%)
Dry RM	152	-	-
Dry KW	8.9	-	-
CRM	133	-	13.0
RK19	20.73	23.21	10.6
RK55	48.69	80.45	39.5
RK91	104.58	137.69	24.0

**Table 4. Concentrations of sodium leachate from the mortars determined in the test and the theoretical values.**

Mortars	Na <sub>test</sub> (mg / L)	Na <sub>theoretical</sub> (mg / L)	Reduction (%)
CRM mix	127.6	-	-
KW mix	5.5	-	-
RK19 mix	7.6	17,8	57.2
RK55 mix	47,7	66.8	28.4
RK91 mix	89.9	115.8	22.3

### 3.4. Color stability in mortars

Table 5 shows the color parameters values periodically measured on 100 cm<sup>2</sup> of each sample before (sub-index 1 = age 1) and after (sub-index 2 = age 2) 8 months exposure to an natural (N) or control (C) environment. The  $\Delta E_{76}$  average values calculated by using those parameters are also shown.

With regard to the color stability, reported that if  $\Delta E_{76}$  values are  $> 1.5$ , color-differences in mortar surfaces can be perceived at naked eye. In line with this statement, the  $\Delta E_{76}$  values of all mortars studied were higher than this limit value, which means that in the natural environment of the Amazon region it is very difficult for the colors of the colored mortars to remain stable over time. However, the results showed that the less noticeable changes in mortar color ( $\Delta E_{76}$  entre 3.50 e 5.7) occurred in those that incorporated pozzolan pigments with a higher percentage of metakaolinite (RK55 and RK19). As seen in item 3.3, the presence of metakaolinite reduced the efflorescence by fixing the sodium in the structure of the products of the pozzolanic reactions, causing not only the increase of the mechanical resistance but also the greater color stability to mortars. In mortars with pigments consisting essentially of calcined RM (CRM and RK91), the perception of the color change was very pronounced, with values of  $\Delta E_{76}$  higher than 9 units. However, the worst result was obtained for the mortar with the incorporation of commercial pigment (BF), with  $\Delta E_{76}$  equal to 13.6. In the environment under controlled conditions of humidity and temperature and without exposure to solar radiation, the color stability is maintained regardless of the type of pigment used.

**Table 5. Color stability in mortars exposed to N and C environments.**

Environment	Mortar	i	L <sub>i</sub>	a <sub>i</sub>	b <sub>i</sub>	C <sub>i</sub>	h <sub>i</sub>	ΔE <sub>76</sub>
N	BF mix	1	45.6	24.4	13.5	27.9	28.3	13.6
		2	50.3	15.1	7,7	16.9	26.9	
N	CRM mix	1	57.7	21.1	19.4	28.7	42.6	12.1
		2	57.5	12.8	10.6	16.6	39.6	
N	RK19 mix	1	74.8	7.6	14.2	16.1	62.0	5.7
		2	71.8	5.2	9.9	11.2	62.4	
N	RK 55 mix	1	63.1	14.4	16.1	21.5	48.1	3.5
		2	61.8	12.3	13.5	18.3	47.5	
N	RK 91 mix	1	58.6	18.4	17.8	25.6	44.0	9.4
		2	59.0	12.2	10.7	16.2	41.2	
C	BF mix	1	45.3	24.3	13.2	27.6	28.5	0.7
		2	45.2	23.7	12.8	26.9	28.4	
C	CRM mix	1	59.0	20.7	19.2	28.3	42.9	2.1
		2	57.9	19.3	18.1	26.4	43.1	
C	RK19 mix	1	73.7	7.6	13.5	15.5	60.6	1.5
		2	74.9	7.2	12.7	14.7	60.4	
C	RK 55 mix	1	58.0	19.1	18.2	24.4	43.7	1.4
		2	58.1	18.1	17.3	25.0	43.8	
C	RK 91 mix	1	61.9	13.8	15.8	21.0	48.9	1.3
		2	63.1	13.8	15.9	21.1	49.0	

Visual assessment of ΔE<sub>76</sub>: 0.5-1.5: slight; 1.5-3.0: obvious; 3-6: very obvious; 6-12: large.

Regarding the luminosity, in the natural environment the ΔL values for the mortars with the pozzolanic pigments ranged from - 0.22 to - 2.9 units whereas for the mortar BF it was of + 4.68 (Figure 7). This means that for the former, the surfaces have become darker because of the deposition of dirt by the wind, a fact that is inevitable. However, in the mortar with the commercial pigment BF the surface became lighter due to the efflorescence (Figure 8). The pigment BF is inert, therefore, it does not react with salts originating from the hydration of the Portland cement that ascends to the surface, whereas the pozzolanic pigments, preferentially those with higher concentrations of metakaolinite (RK55 and RK19), mitigate the efflorescence due to the pozzolanic reactions. Under controlled laboratory conditions, there were practically no changes in the luminosity of the surfaces of all the mortars studied.

With regard to Δa, parameter that expresses the red color, regardless of the environment, the pigment BF provided a higher value of a\* for the mortar, which means a greater red color intensity compared to the pozzolan pigments. This is due to the higher concentration of hematite in the commercial pigment composition. However, pozzolan pigments compensate for the loss in hue with a greater replacement of Portland cement since they allow this because of the higher mechanical strengths. In the natural environment the mortars with pozzolanic pigments presented negative variations between 2 and 8 whereas the one with pigment BF the negative variation was superior to 9 units. This means that the originally red color was substantially altered due to efflorescence and deposition of particulates. The results again demonstrate that pozzolan pigments provide greater color stability than the commercial BF pigment.

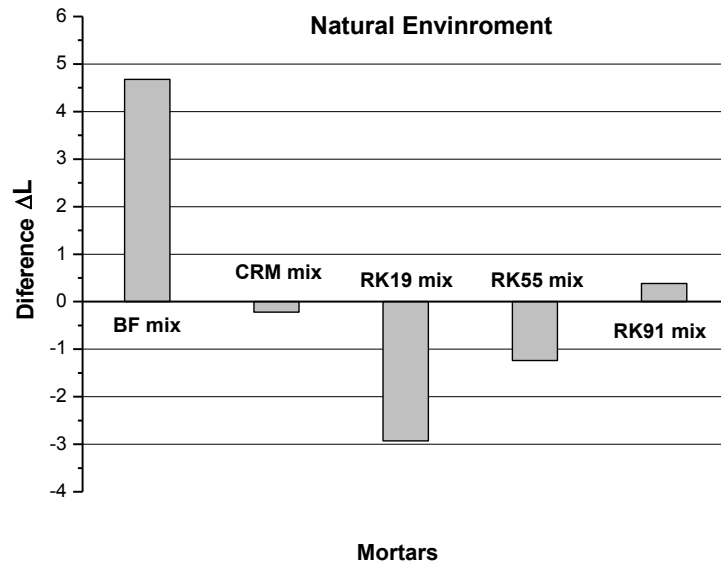


Figure 7. ΔL in mortars.

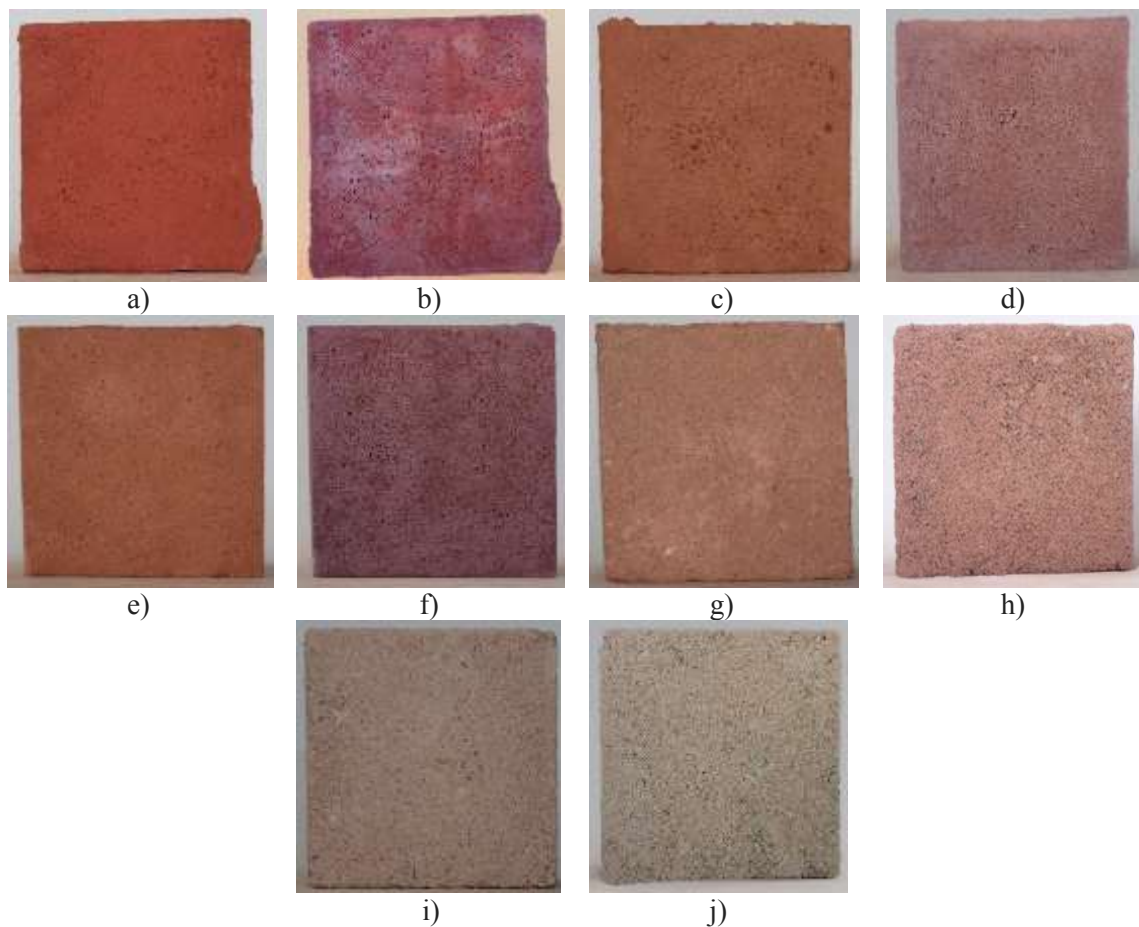


Figure 8. Color changes of BF mortar and with pozzolanic pigments during 8 months of exposure to the natural environment: a) and b) BF mix at 1 and 238 days; c) and d) CRM mix at 1 and 238 days; e) and f) RK91 mix at 1 and 238 days; g) and h) RK55 mix at 1 and 238 days; i) and j) RK19 at 1 and 238 days.

#### 4. Conclusions

The incorporation of pozzolanic pigments from RM and KW mixtures has provided substantial increases in compressive strength compared to commercial BF pigments, which is extremely advantageous for the case of colored concrete flooring.

The pozzolanic pigments reduced the concentrations of sodium leachate in the mortars due to the presence of metakaolinite, which through the pozzolanic reactions promotes the stabilization of the chemical element by solidification.

As a result of this mitigation of sodium leaching, pozzolanic pigments also provided greater color stability to mortars compared to commercial pigment BF.

The pozzolanic pigments showed superior behavior to the commercial pigment in terms of mechanical resistance, reduction of sodium leaching and greater color stability due to the reduction of efflorescence. Only the color intensity was lower, however, this aspect can be mitigated with greater incorporations of pozzolanic pigment without prejudice to the mechanical properties.

In summary, the results demonstrate the promising character of the RM-KW mixtures for the production of pozzolanic pigments as well as mineral admixture for pozzolanic cements of excellent durability and mechanical behavior.

#### 5. References

1. M.S. Barata, Concreto de alto desempenho no Pará: Estudo da viabilidade técnica e econômica de produção de concreto de alto desempenho com os materiais disponíveis em Belém através do emprego de adições de sílica ativa e metaaulim. 1998, 165p. Dissertação (Mestrado em Engenharia Civil), Programa de Pós-graduação em Engenharia Civil. Universidade Federal do Rio Grande do Sul, Porto Alegre.
2. S.M.P. Flores, Aproveitamento do rejeito de caulim na produção de alumina para cerâmica e sílica de baixa granulometria. 2000. 191p. Tese (Doutorado em Geologia e Petrologia). Curso de Pós-Graduação em Geologia e Geoquímica, Centro de Geociências. Universidade Federal do Pará, Belém.
3. J.M. Lima, Estudo do aproveitamento do resíduo do beneficiamento de caulim como matéria prima na produção de pozolanas para cimentos compostos e pozolânicos. 2004. 107p. Dissertação (Mestrado em Engenharia Civil), Programa de Pós-graduação em Engenharia Civil, Universidade Federal do Pará, Belém.
4. P.S.L. Souza, Verificação da influência do uso de metacaulim de alta reatividade nas propriedades mecânicas do concreto de alta resistência. 2003. 203p. Tese (doutorado em Engenharia Civil), Programa de Pós-graduação em Engenharia Civil. Universidade Federal do Rio Grande do Sul, Porto Alegre.
5. M.C. Martelli, Transformações térmicas e propriedades cerâmicas de resíduos de caulins das regiões do Rio Capim e do Rio Jari. 2006. 160p. Tese (Doutorado em Geologia e Petrologia). Curso de Pós-Graduação em Geologia e Geoquímica, Centro de Geociências. Universidade Federal do Pará, Belém.
6. F.S.S. Lima, Utilização da lama vermelha e do resíduo caulínico na produção de pigmento pozolânico para argamassas e concretos de cimento Portland. 2006. 133p. Dissertação (Mestrado em Engenharia Civil), Programa de Pós-graduação em Engenharia Civil, Universidade Federal do Pará, Belém.
7. M.S. Barata, Aproveitamento dos resíduos caulínicos das indústrias de beneficiamento de caulim da região amazônica como matéria-prima para fabricação de um material de

- construção. 2007. 396p. Tese (Doutorado em Geologia e Petrologia). Programa de Pós-Graduação em Geologia e Geoquímica da Universidade Federal do Pará, Belém.
8. E.A. Hildebrando, Aplicação do rejeito do processo Bayer (lama vermelha) como matéria-prima na indústria de cerâmica estrutural. 1998. 82p. Dissertação (Mestrado em Engenharia Química). Departamento de Engenharia Química, Universidade Federal do Pará, Belém.
  9. R.A. Hind, S.K. Bhargava, S.C. Grocott, The surfasse chemistry of Bayer process solids: a review, *colloids and surfaces A: Phsicochemical and engineering aspects* 1999, 359-374.
  10. A. Collazo, D. Fernandez, M. Izquierdo, X.R. Nóvoa, C. Perez, Evaluation of red mud as surface treatment for carbon steel painting, *Process in Organic Coating* 2005, 351-358.
  11. E.B. Silva Filho, M.C. Alves, M. Da Motta, Estudo sobre a utilização da lama vermelha para a remoção de corantes em efluentes têxteis, *Revista Matéria*. Vol. 12, No. 2, (2007), 322-38.
  12. J. Pera, R. Boumaza, J. Ambroise, Development of a pozzolanic pigment form red mud, *Cement and Concrete Research*. Vol. 27, No. 10, (1997), 1513-1522.
  13. C. Dow, F.P. Glasser, Calcium carbonate efflorescence on Portland cement and building materials, *Cement and Concrete Research*. Vol. 33, (2003), 147-154.
  14. R.D. Lozano, El Color Y Su Medición, Américalee S.R.L., Buenos Aires, 1978.
  15. CIE 15.3 Technical report draf, 3rd ed., Colorimetry, 2004.
  16. G. Teichmann, The use of colorimetric methods in the concrete industry, *Betonwerk + Fertgteil-Technik/Concr. Precast. Plant Technol.* 1990, 58-73.
  17. EN 12878, Pigments for Colouring of Building Materials Based on Cement and/or Lime – Specification and Methods of Test, 2005.