

Effect of Vanadium Ion Impurity on the Adsorption of Gallium on Resin

Guan Xiaoge¹, Zhang Chao², Han Xiaobo³ and Wei Shuyao⁴

1. Middle Engineer

2. Middle Engineer

3. Junior Engineer

4. Middle Engineer

Zhengzhou Non-ferrous Metals Research Institute Ltd of CHALCO, Henan, China, 450041

Corresponding author: 1546902951@qq.com

Abstract

DOWNLOAD
FULL PAPER



Gallium is widely applied in solar energy, semiconductor, biology and chemical industry; it accounts for 80–85 % of the world's semiconductor applications. 95 % of the primary gallium originates from bauxite. Therefore, extracting and recovering gallium from bauxite has become a significant research topic. At present, gallium extraction is mainly carried out by resin adsorption method in industry. However, there are a large number of co-existing ions in the gallium-enriched solution, which can have an adverse effect on the process of gallium adsorption on the resin; such is especially the case of vanadium, which competes with gallium on the functional groups of the resin. Therefore, it is necessary to study the influence of vanadium on the gallium adsorption process.

Keywords: Bauxite, resin adsorption , gallium, vanadium

1. Introduction

Gallium has an important application in the semiconductor industry. With the development of new technologies and the demand for metal gallium in various applications, processes to efficiently and quickly produce gallium are in high demand. In recent years, China's compound wafer industry, mainly composed of gallium arsenide, has rapidly expanded and grown rapidly, resulting in a sharp increase in demand for gallium. At present, about 90 % of the world's gallium is recovered from the production process of alumina, while the remaining small amount of gallium is extracted from leaching zinc slag, iron slag, and fly ash. China is a major global alumina and aluminum producer; the weight percentage of gallium in the ore used for alumina production is about 0.007 %. Gallium exists in the spent Bayer liquor in the form of sodium galliate and continuously enriches, with an equilibrium concentration of up to 100–300 ppm [2–4]. Scholars have conducted in-depth research on how to enrich and purify gallium from the sodium aluminate liquor to obtain metallic gallium.

Ion exchange technology is an effective method for extracting gallium [5–7]. There are many known selective ion exchange resins, namely chelating resins, which have high capacity and selectivity compared to certain metals. Such resins have atoms such as O, N, S, P, As with lone pair electrons. The lone pair electrons of these atoms form coordinate covalent bonds with metal ions [8], forming a stable structure similar to a small molecule chelation. This has the advantages of large adsorption capacity, strong selectivity and stable properties. Therefore, the application of ion-exchange resins may enable the selective extraction of gallium ions from process liquors and the subsequent production of metallic gallium.

2. Mechanism of Resin Adsorption of Gallium

The extraction of gallium from the sodium aluminate liquor using a resin mainly relies on the active functional groups present in the resin structure, such as =NOH, NH, -OH, -SH, =NH, and so on. Because the atoms in these active functional groups have unbound lone pairs of electrons, they can form coordinate covalent bonds with gallium ions, generating stable structures similar to small molecular complexes, and realize the adsorption of gallium by resins. Currently, there is a mainstream mechanism for the binding of gallium ions on the resin: Gallium ion generally exists in the form of $\text{Ga}(\text{OH})_4^-$ in an alkaline solution. When $\text{Ga}(\text{OH})_4^-$ is adsorbed by the resin, H^+ on the hydroxyl group of =N-OH is released, and then the remaining oxygen atom forms a coordinate covalent bond with gallium. However, there may be no coordination reaction between Ga and N. At the same time, the released H^+ will combine with an OH^- from $\text{Ga}(\text{OH})_4^-$ to generate H_2O . Therefore, it can be considered that the oxygen binding mode may be the main mode of binding between resin and gallium ions in solution [9–12]. The possible reaction between =N-OH and $\text{Ga}(\text{OH})_4^-$ in amidoxime is shown in the following equation:

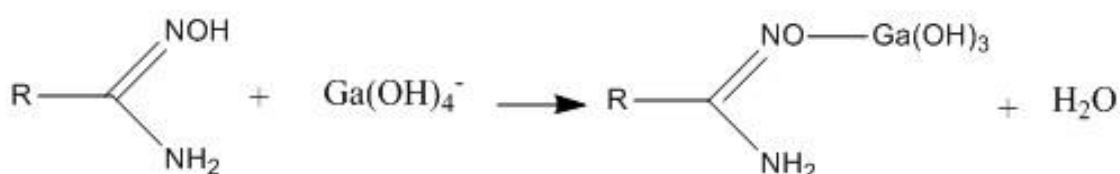


Figure 1. Resin adsorption of gallium

3. Effect of Vanadium on Resin Adsorption of Gallium

3.1 Mechanism of Resin Adsorption of Vanadium

Due to the presence of a large amount of impurities in sodium aluminate solution, this will inevitably have a negative impact on the process of gallium adsorption by resin, especially with the case of vanadium ion. Zheng Qi [3] conducted FT-IR and XPS analysis on the resin and found that there was a cross adsorption of gallium and vanadium on the resin. Gallium ion in alkaline solutions only interact with the oxime group in the resin, while vanadium ion reacts with the oxygen atoms of the oxime group (C=NOH) in the resin and the nitrogen atoms of the amino group (C-NH₂), which leads to a stronger interaction force between vanadium ion and the resin, which in turn makes it difficult for vanadium ion to desorb from the resin. Therefore, gallium and vanadium form competitive adsorption, and the adsorption of vanadium by the resin will reduce the adsorption capacity of the resin for gallium. Vanadium ion mainly exists in the form of VO_4^{3-} in strong alkaline solutions [13–14], so the possible reaction formula between vanadium ions and effective groups in the resin is as follows:

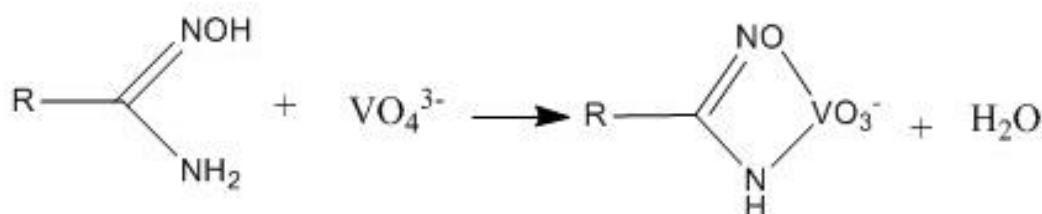


Figure 2. Resin adsorption of vanadium

In addition, as the concentration of vanadium increases, the resin changes from light yellow to dark brown. Due to the resin adsorbing gallium, a considerable amount of vanadium is also adsorbed and difficult to desorb. As a result, vanadium gradually accumulates in the resin during cycling and occupies the corresponding functional positions in the resin, reducing the

accumulation of vanadium ions on the resin, the resin is regularly "purified" to remove vanadium, restoring the effective group positions on the resin.

When discussing the mechanism, it was found that the adsorption capacity of V rapidly increases at low concentrations, while the change of Ga is not significant; At higher concentrations, the adsorption rate of Ga is much faster than that of V. Therefore, within a short period of contact between the solution and the resin, most of Ga ions are adsorbed on the resin, while the adsorption amount of V is much smaller. As time goes on, the adsorption capacity of V ions will gradually increase, which will greatly hinder the resin's adsorption of gallium. It can be inferred that the shorter the contact time, the more favorable it is for the resin to adsorb gallium. Therefore, during the dynamic adsorption process of the resin, a certain range of high spent Bayer liquor flow rate and short contact time are beneficial for the adsorption of Ga.

In the previous chapters, it is known that the adsorption of gallium and vanadium by resin is an endothermic process, and an increase in temperature is beneficial for the adsorption of gallium and vanadium. The adsorption rate of Ga ion varies slightly with temperature changes, while V ions are sensitive to temperature changes, and the adsorption rate of V ion increases with temperature, which may be related to their chemical properties [3]. Therefore, by adjusting the temperature within a lower range, the adsorption of vanadium by the resin can be reduced.

In addition, during the desorption process, Ga ions are almost completely desorbed in acidic solutions, while V ions are hardly desorbed. Therefore, acidic desorption solution is used to reduce the desorption of vanadium and achieve the separation of the two metals; Secondly, it can be seen from the test data that V ions are more sensitive to the change of alkali concentration, showing the opposite trend when the concentration of sodium hydroxide changes, and the adsorption capacity decreases with the increase of alkali concentration, but the change of alkali concentration has little effect on Ga ion, which indicates that the resin can be washed regularly with concentrated alkali solution to reduce the accumulation of vanadium, however the strongly alkaline desorption solution cannot make V ion completely desorbed, and it may only achieve the purpose of extending the service life of the resin.

5. Conclusions

The strong alkaline conditions in the alumina production process and the complexity of solution composition make the resin adsorption of gallium susceptible to impurities. This article discusses why the resin adsorbs vanadium ions and how to reduce the impact of vanadium ions. Resin adsorption is a complex physical and chemical process, which requires comprehensive consideration of various influencing factors to guide the actual production process. Further in-depth research is needed in the future.

6. References

1. V. N. Sagdiev, et al., Process of extraction of gallium from technological solutions with the use of ion exchange resins, *Metallurgist*, 2019, 63:206-214
2. Lu Siming, Studies on the recovery of gallium from bayer solution by resin sorption method, Guangxi University
3. Zheng Qi, Adsorption and separation of gallium and vanadium by macroporous amidoxime chelating resin and its mechanism, Guangxi University
4. Lu Fang hai, et al. Recovery of Low Concentration Gallium from Alkaline Solution, *Nonferrous Metals*, 2018, 11:34-38
5. P. Bermejo-Barrera, et al. Separation of gallium and indium from ores matrix by sorption on Amberlite XAD-2 coats with PAN, *Fresenius' Journal of Analytical Chemistry*, 2001,2: 191-194

6. Liu Junshen, et al. Separation of indium(III), gallium(III), and zinc(II) with Levextrel resin containing di(2-ethylhexyl) phosphoric acid (CL-P204): Part II. Mechanism and kinetics of adsorbing indium(III), *Rare Metals*, 2004, 1:1-5
- [1] Yang Limei, Li,ling, et al. Adsorption of Chelate Resin D412 on Ni²⁺, Fe²⁺, Fe³⁺ Ions in Aqueous Solutions[J], *Chinese Journal Rare Metals*, 2009, 33: 401-405
- [2] Zhao Yisen, Study on the recovery process of gallium in the Bayer red mud, North University Of China
- [3] Feng Feng, Li Yifan, Effect of Bayer Process Solution Composite on Adsorbing Galliumby Resin[J], *Hydrometallurgy of China*, 2006, 25:30-32
- [4] Zhao Zhuo, et al. Adsorption Performances and Mechanisms of Amidoxime Resin toward Gallium(III) and Vanadium(V) from Bayer Liquor, *ACS Sustainable Chemistry & Engineering*, 2015, 1: A-G
- [5] Long Hongming, et al. Binding Mechanism of the Amidoxime Functional Group on Chelating Resins toward Gallium(III) in Bayer Liquor, *Industrial & Engineering Chemistry Research*, 2015, 8025-8030
- [6] K Srinivasa Rao, D Sarangi, Preferential extraction of gallium from Bayer liquor using ion exchange chelating resin containing hydroxamic acid functional group, *Journal of Chemical Technology and Biotechnology*, 2003, 78:555-561
- [7] P.A. Riveros, Recovery of gallium from Bayer liquors with an amidoxime resin, *Hydrometallurgy*, 1990, 25:1-18
- [8] Zhao zhuo, et al. Study of adsorption property of Ga(III) onto strongly basic resin for Ga extraction from bayer liquor, *The Minerals, Metals & Materials Society*, 2013, 27-35
- [9] Jing Xiaosheng, et al. Adsorption performances and mechanisms of the newly synthesized N, N'-di (carboxymethyl) dithiocarbamate chelating resin toward divalent heavy metal ions from aqueous media, *Journal of Hazardous Materials*, 2009, 167:589-596