

Research and Application of Advanced Energy-Saving Technology for Aluminum Reduction Cells

Quanlin Li¹, Yungang Ban², Jian Zhang³, Yubing Wang⁴, Hongwu Hu⁵ and Ping Wang⁶

1. Junior Project Manager

4. Project Manager

5. Process Director

Shandong Hongtuo Industrial Co., Ltd., Binzhou, China

2. Process Director, Senior Engineer

NEUI, Northeastern University Engineering & Research Institute Co., Ltd., Shenyang, Liaoning, China.

3. Project Manager

NFC, China Nonferrous Metal Industry's Foreign Engineering & Construction Co., Ltd., Beijing, China

6. Project Manager

Tokai COBEX GmbH, Wiesbaden, Germany

Corresponding author: banyungang@126.com

Abstract



In the current global carbon footprint reduction efforts, primary aluminum industry has attracted much attention. The annual huge electricity consumption of the Chinese aluminium reduction industry accounts for 6.5 % of the total electricity consumption of the whole society in China. Under the pressure of national policies, China's aluminum reduction industry is accelerating its low-carbon and green transformation. In recent years, NFC/NEUI has successively developed a series of energy-saving technologies for aluminum reduction cells, mainly including new energy-saving anode technology, RuC and copper insert cathode energy-saving technology, magnetic fluid super stability technology, thermal balance optimization design technology, etc. These energy-saving technologies are gradually being promoted and applied in 400 kA, 500 kA, and 600 kA aluminum reduction cells in China. Taking the application of RuC technology in 600 kA as an example, it achieved a DC energy consumption of 12 287 kWh/t Al, which achieved significant energy-saving effects compared to saving 566 kWh/t Al.

Keywords: Aluminum reduction cell technology, Research and application of energy-saving technology, Low energy consumption in aluminum reduction cells.

1. Introduction

China is actively adopting stronger policies and measures, aiming to peak carbon dioxide emissions by 2030 and achieve carbon neutrality by 2060. By 2030, China's carbon dioxide emissions per unit of GDP will decline by more than 65 % compared with 2005, the proportion of non-fossil energy in primary energy consumption will reach about 25 %, the forest stock will increase by 6 billion cubic meters compared with 2005, and the total installed capacity of wind power and solar power generation will reach more than 1200 GW.

On August 27, 2021, the National Development and Reform Commission issued a comprehensive tiered electricity pricing policy for the aluminum reduction industry, encouraging aluminum reduction enterprises to improve the utilization level of non-water renewable energy such as wind power and solar power generation, and reduce fossil fuel consumption. In order to promote energy conservation and emission reduction in the aluminum reduction industry, the National Development and Reform Commission has gradually established a differentiated electricity price policy for the aluminum reduction industry. Starting from 2023, the comprehensive AC energy

consumption of liquid aluminum is lower than 13 450 kWh/t Al (excluding desulfurization energy consumption). Starting from 2025, the comprehensive AC power consumption of liquid aluminum is lower than 13 300 kWh/t Al (excluding desulfurization power consumption). Chinese aluminum companies are actively searching for technologies and ideas to further reduce aluminum reduction energy consumption.

In 2022, China's primary aluminum production reached 40.214 million tonnes, accounting for 6.5 % of the total electricity consumption of 8637.2 TWh in 2022. The peak production capacity of primary aluminum has become one of the key industries for carbon emissions peaking. In recent years, the national supply side reform has achieved results, with limited increase in production capacity on the supply side, increased demand for clean energy aluminum on the demand side, and tight supply and demand leading to a high aluminum per tonne profit market. Opportunities and challenges coexist.

The central task for aluminum smelters is to achieve carbon dioxide emission reduction by reducing the overall AC power consumption to less than 13 300 kWh/t Al (excluding desulfurization energy consumption) in 2025; this is the key to the survival of the smelters.

2. Research and Development of Energy-saving and Low-carbon Technologies in China

Since entering the new century, China has made significant progress in the core technology of primary aluminum, with internationally leading technology for high amperage cells. 600 kA aluminum cell technology has been widely applied, and the average energy consumption per unit product has shown a significant downward trend overall. In 2020, the industry's average comprehensive AC power consumption was 13 543 kWh/t Al, a decrease of 500 kWh/t Al compared to 2013.

In recent years, under the requirements of the national energy consumption “dual carbon” policy, one to peak emissions before 2030, and the other to achieve carbon neutrality before 2060, scientific and technological workers in China's aluminum reduction industry have made continuous efforts to develop energy-saving technologies for the cathode structure of aluminum reduction cells, such as graphitized cathode blocks, graphitized cathode blocks with cast iron assembly, large cross-section high conductivity collector bars, copper insert collector bars, etc., which have achieved varying degrees of energy-saving effects in different application scenarios.

3. RuC Technology Research and Application in China

In order to achieve further energy saving and carbon reduction, Shandong Weiqiao group, NEUI, Tokai COBEX and NFC collaborated to develop the “RuC energy-saving, long life, and high yield aluminum technology” with Tokai COBEX patented ready to use cathode (RuC) technology as the core [1, 2].

The RuC stability in cathode voltage drop (CVD) with low electrical contact resistance is achieved despite the lower contact surface area (- 60 %) compared to conventional cathodes. The low level and stable trend of CVD proves the robustness of the cathodic system [3].

This technology has been undergoing industrial trials on NEUI 400 kA and NEUI 600 kA aluminum reduction cells of Weiqiao Group since December 2016, achieving significant energy-saving, production increase, and pot life extension. In order to better respond to the policy requirements of “dual control” of energy consumption and lead industry technological progress, Weiqiao group has started to accelerate the expanded application of RuC technology in 600 kA potlines.

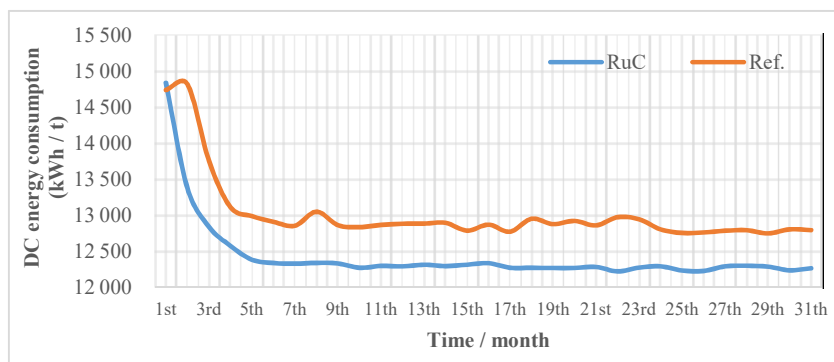


Figure 6. Comparison of DC energy consumption between two 600 kA RuC and reference cells.

4. Conclusions

The new energy-saving and long cell life technology of RuC for aluminum electrolysis developed in this project has achieved industry-leading main technical and economic indicators through application in 600 kA reduction cells.

It is currently the most promising energy-saving technology in the industry, which can achieve significant energy-saving, carbon reduction, and extended cell life. RuC technology plays an important role in promoting technological progress and innovation in the industry, more large-scale applications are underway in China.

5. References

1. Sum Elaine et al., Cathode assembly for the production of aluminum, *EP3491175A1*, filed July 26, 2017, granted June 05, 2019.
2. Markus Pfeffer et al., Cathode current collector/connector for a Hall-Heroult cCell: *CN109863258A*, filed July 26, 2017, granted May 31, 2022.
3. Markus Pfeffer et al., A novel cathode design using copper collector bars for high amperage technologies, *Proceedings of 39th International ICSOBA Conference, Virtual Conference*, 22–24 November 2021, *TRAVAUX 50*, 793-801.
4. Markus Pfeffer et al., Ready-to-use cathodes in high amperage technologies, *Light Metals 2022*, 946-953.